



Designation: D4585/D4585M – 18

Standard Practice for Testing Water Resistance of Coatings Using Controlled Condensation¹

This standard is issued under the fixed designation D4585/D4585M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope*

1.1 This practice covers basic principles and operating procedures for testing water resistance of coatings using controlled condensation. Condensation is produced by exposing one surface of a coated specimen to a heated, saturated mixture of air and water vapor, while the reverse side of the specimen is exposed to the cooling effect of room temperature air. This practice is derived from research of the Cleveland Society for Coatings Technology.²

1.2 This practice is limited to the methods of obtaining, measuring, and controlling conditions and procedures of controlled condensation tests. It does not specify specimen preparation, specific test conditions, or evaluation of results.

NOTE 1—Alternative practices for testing water resistance of coatings include Practices [D870](#), [D1735](#), and [D2247](#).

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This practice is under the jurisdiction of ASTM Committee [D01](#) on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee [D01.27](#) on Accelerated Testing.

Current edition approved July 1, 2018. Published July 2018. Originally approved in 1986. Last previous edition approved in 2013 as D4585 – 13. DOI: 10.1520/D4585_D4585M-18.

² Foecking, N. J., “Cleveland Condensing Type Humidity Cabinet,” *Official Digest*, December 1963, Vol 35, No. 467, pp. 1318–1327; and Higgins, W. A., “Cleveland Condensing Type Humidity Cabinet: II,” *Official Digest*, November 1965, Vol 37, No. 490, pp. 1392–1404.

2. Referenced Documents

2.1 ASTM Standards:³

- [D609 Practice for Preparation of Cold-Rolled Steel Panels for Testing Paint, Varnish, Conversion Coatings, and Related Coating Products](#)
- [D610 Practice for Evaluating Degree of Rusting on Painted Steel Surfaces](#)
- [D714 Test Method for Evaluating Degree of Blistering of Paints](#)
- [D823 Practices for Producing Films of Uniform Thickness of Paint, Coatings and Related Products on Test Panels](#)
- [D870 Practice for Testing Water Resistance of Coatings Using Water Immersion](#)
- [D1654 Test Method for Evaluation of Painted or Coated Specimens Subjected to Corrosive Environments](#)
- [D1730 Practices for Preparation of Aluminum and Aluminum-Alloy Surfaces for Painting](#)
- [D1735 Practice for Testing Water Resistance of Coatings Using Water Fog Apparatus](#)
- [D2247 Practice for Testing Water Resistance of Coatings in 100 % Relative Humidity](#)
- [D2616 Test Method for Evaluation of Visual Color Difference With a Gray Scale](#)
- [D3359 Test Methods for Rating Adhesion by Tape Test](#)
- [D3363 Test Method for Film Hardness by Pencil Test](#)
- [D4541 Test Method for Pull-Off Strength of Coatings Using Portable Adhesion Testers](#)
- [G154 Practice for Operating Fluorescent Ultraviolet \(UV\) Lamp Apparatus for Exposure of Nonmetallic Materials](#)

3. Summary of Practice

3.1 Water vapor is generated by heating a pan of water at the bottom of the test chamber. The specimens form the roof or walls of the test chamber so that the back sides of the specimens are exposed to the cooling effects of room temperature air. The resulting heat transfer causes vapor to condense on the test specimens as liquid water saturated with air.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

3.2 The temperature and amount of condensate forming on the specimens is controlled by the temperature differential between the test chamber and the room. The test specimens are inclined so that condensate runs off the test surface by gravity and is replaced by fresh condensate in a continuous process during the condensate cycle.

3.3 Exposure conditions are varied by selecting: (a) the temperature of the test, (b) the duration of the test, and (c) periodic drying of the specimens. Testing may be conducted at temperatures from 38 to 82°C [100 to 180°F]. Any effects such as color change, blistering, loss of adhesion, softening, or embrittlement are observed and reported.

4. Significance and Use

4.1 Water can cause degradation of coatings, so knowledge of how a coating resists water is helpful in predicting its service life. Failure in a condensation test may be caused by a number of factors including a deficiency in the coating itself, contamination of the substrate, or inadequate surface preparation. The test is therefore useful for evaluating coatings alone or complete coating systems.

4.2 Condensation tests of coatings are used for specification acceptance, quality control, and research and development of coatings and substrate treatments. These tests usually result in a pass or fail determination but the degree of failure also may be measured. A coating system is considered to pass if there is no evidence of water-related failure after a specified period of time.

4.3 Results obtained from the use of condensation tests in accordance with this practice should not be represented as being equivalent to a period of exposure to water in the natural environment, until the degree of quantitative correlation has been established for the coating or coating system.

4.4 The test is usually conducted on metal, plastics, or wood specimens with the coating facing the inside of the chamber. However, it is possible to test the blister resistance of house coatings on wood specimens by mounting the uncoated wood surface facing the inside of the chamber.

4.5 This practice can be used for corrosion tests particularly if the specimens are periodically dried. While corrosion products will drain into the water bath, they are not carried into the vapor that condenses on the test specimens.

5. Apparatus

5.1 *Test Chamber* (see Fig. 1 and Fig. 2), consisting of

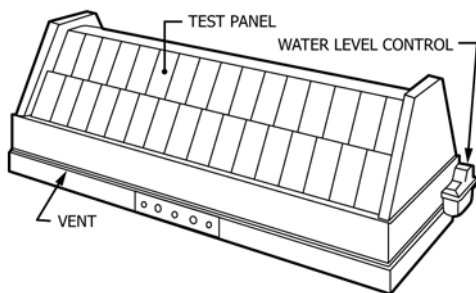


FIG. 1 Controlled Condensation Apparatus

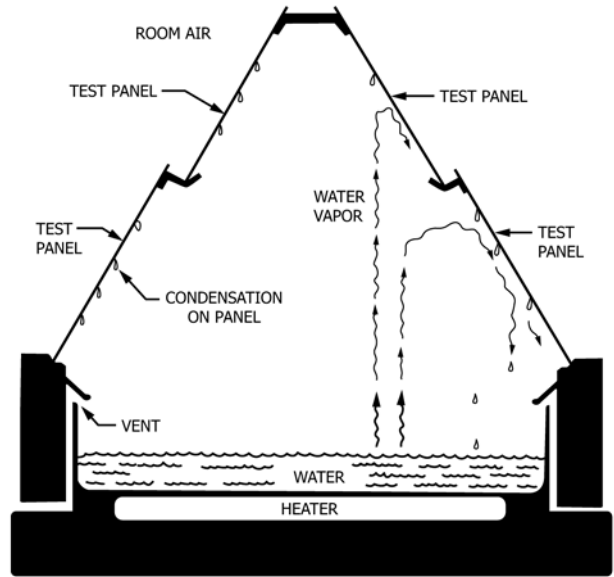


FIG. 2 Apparatus Cross Section

insulated side walls mounted on a base, test specimen racks attached to the side walls, a heated water pan, and provisions for controlling and indicating the vapor temperature within the chamber. Vents, approximately 3 to 5 mm [0.10 to 0.20 in.] wide, shall be provided to admit room air at the bottom of the test chamber. Locate the chamber away from air vents and direct drafts.

NOTE 2—The apparatus described in Practice G154 may be used if the ultraviolet lamps specified in Practice G154 are turned off.

5.2 Specimens shall form the roof of the test chamber. If the specimens cannot completely fill all the openings, blank panels shall be used. Certain substrates may deform from the heat and moisture. The specimens shall be mounted to eliminate gaps between specimens that allow heat and moisture to escape. Various types of tape can be used to seal the gaps that develop when the specimen deforms. Specimens shall be inclined from 15 to 75° from the horizontal and arranged so that condensate is returned to the water pan without dripping on other specimens.

5.3 *Water Supply*, with water level control.

5.4 *Water Heater*, preferably located under the water pan, controlled by a thermostat with the sensing element located in the water.

5.5 *Thermometer*, with the stem extending into the air-water vapor mixture in the test chamber.

5.6 *Program Timer, Blower, and Air Heater*, (optional) fitted to the chamber to provide periods of drying on a fixed schedule.

6. Test Specimens

6.1 This practice does not cover the preparation of test specimens. The substrate composition and surface preparation, specimen preparation, and the number of specimens should be agreed upon prior to testing.

NOTE 3—Applicable methods for the preparation of test panels and