



Designation: D5262 – 21

Standard Test Method for Determining the Unconfined Tension Creep and Creep Rupture Behavior of Planar Geosynthetics Used for Reinforcement Purposes¹

This standard is issued under the fixed designation D5262; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method is intended for use in determining the unconfined tension creep and creep rupture behavior of geosynthetics at constant temperature when subjected to a sustained tensile loading. This test method is applicable to all geosynthetics.

1.2 The test method measures total elongation of the geosynthetic test specimen, from the time of loading, while being maintained at a constant temperature. It includes procedures for measuring the tension creep and creep rupture behavior at constant temperature of conditioned unconfined geosynthetics as well as directions for calculating tension forces to plot creep and creep rupture curves.

1.3 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D123 Terminology Relating to Textiles](#)

¹ This test method is under the jurisdiction of ASTM Committee D35 on Geosynthetics and is the direct responsibility of Subcommittee D35.02 on Endurance Properties.

Current edition approved Feb. 15, 2021. Published February 2021. Originally approved in 1992. Last previous edition approved in 2016 as D5262 – 07 (2016). DOI: 10.1520/D5262-21.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standards' Document Summary page on the ASTM website.

[D1776/D1776M Practice for Conditioning and Testing Textiles](#)

[D2990 Test Methods for Tensile, Compressive, and Flexural Creep and Creep-Rupture of Plastics](#)

[D4354 Practice for Sampling of Geosynthetics and Rolled Erosion Control Products \(RECPs\) for Testing](#)

[D4439 Terminology for Geosynthetics](#)

[D4595 Test Method for Tensile Properties of Geotextiles by the Wide-Width Strip Method](#)

[D6637/D6637M Test Method for Determining Tensile Properties of Geogrids by the Single or Multi-Rib Tensile Method](#)

[E6 Terminology Relating to Methods of Mechanical Testing 2.2 ISO Standard:](#)³

[ISO/TR 20432 Guidelines for the Determination of the Long-Term Strength of Geosynthetics for Soil Reinforcement](#)

3. Terminology

3.1 For definitions of many terms used in this test method, refer to Terminologies [D123](#), [D4439](#), and [E6](#).

4. Summary of Test Method

4.1 The tension creep and creep rupture behavior of unconfined geosynthetics is measured by applying a sustained load in one step and measuring the total elongation of the test specimen as a function of time while maintaining a specified temperature and humidity.

5. Significance and Use

5.1 This test method is developed for use in the determination of anticipated total elongation over time or time to rupture that may occur in geosynthetics under sustained loading conditions.

5.1.1 The test data can be used in conjunction with interpretive methods to determine creep strain potential at design loads.

³ Available from International Organization for Standardization (ISO), ISO Central Secretariat, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <https://www.iso.org>.

5.1.2 The test data can be used in conjunction with interpretive methods to determine creep rupture potential at various loads.

5.2 This test method is not intended for routine acceptance testing of geosynthetics. This test method should be used to characterize geosynthetics intended for use in reinforcement applications in which creep or creep rupture is of concern. The plane strain or rupture condition imposed during testing must be considered when using the test results for design.

5.3 The basic distinctions between this test method and other test methods for measuring tension creep and creep rupture behavior are: (1) the width of the specimens (Section 8), and (2) the measurement of total elongation over time or time to rupture from the moment of specimen loading. The greater widths of the specimens specified in this test method minimize the contraction edge effect (necking) that occurs in many geosynthetic materials and provides a closer relationship to actual material behavior in plane strain tension conditions.

5.4 The creep or stress rupture of a given geosynthetic is likely to be reduced in soil because of confining stresses and load transfer to the soil. The unconfined environment represents a controlled test in which the results are conservative with regard to the behavior of the material in service. Confined or in-soil testing may model the field behavior of the geosynthetic more accurately.

6. Apparatus

6.1 Clamps:

6.1.1 Clamps should be at least as wide as the specimen, with appropriate clamping power that will prevent slipping or damage of the test specimen within or at the faces of the clamps. The clamps and clamping technique shall be designed to minimize eccentric loading of the specimen. A swivel or universal joint shall be used on one of the clamps at the end of the specimen. It is recommended that clamps permit the final centering of the specimen prior to application of the load.⁴

6.1.2 *Geotextiles and Geomembranes*—Each clamp shall be sufficiently wide to grip the entire width of the specimen, 200 mm (8.0 in.), and a minimum of 50 mm (2.0 in.) length in the direction of the applied force.

6.1.3 *Geogrids*—These should be clamped to ensure complete tension load transfer through test direction members. The type of clamp and load transfer mechanism should be detailed in the test report. Roller grips or low melting point alloy with adequate strength may be used to assist proper clamping. See Test Method [D6637/D6637M](#).

6.1.4 *Other Related Products*—Where special clamps are used to grip these products, they should conform to the general requirements for clamps used to grip geotextiles, geomembranes, and geogrids, and the clamping methods used should always be detailed in the report.

6.2 *Loading System*—The loading system must be designed so that the load applied and maintained on the specimen is within $\pm 1\%$ of the desired load. Loads may be applied by

weights, weights and fulcrums, hydraulics, or pneumatics. The loading mechanism must permit reproducibly rapid and smooth loading, as specified in [11.5](#). No dynamic forces on placement of the loads shall be allowed. Provision must also be made to ensure that shock loading caused by specimen failure is not transferred to other specimens undergoing testing.⁴ If a non-weight or gravity system is used to apply the load, a backup system shall be available to ensure continuity of load application. The type of backup system available shall be described in the report.

6.3 *Extension Measurement*—LVDTs or dial gauge extensometers are preferred for the measurement of elongation in geosynthetics when testing specimens with short gauge lengths. Whenever possible, other means of measuring elongation should be calibrated against extensometers. In any case, the device chosen shall be capable of measuring deformations to an accuracy of at least 0.1 % of the gauge length of the specimen. The means of measuring elongation should be indicated clearly in the report.

6.4 *Vibration Control*—Creep and creep rupture tests are sensitive to shock and vibration. The location of the apparatus, test equipment, and mounting shall be designed so that the specimen is isolated from vibration. Multi-station test equipment must be of sufficient rigidity so that no significant deflection due to shock or vibration occurs during testing.

6.5 *Time Measurement*—The accuracy of the time measuring device shall be $\pm 1\%$ of the elapsed time of each creep or creep rupture measurement load increment.

6.6 *Temperature Control and Measurement:*

6.6.1 The temperature in the test space, especially close to the gauge length of the specimen, shall be maintained within $\pm 2.0\text{ }^\circ\text{C}$ ($\pm 3.6\text{ }^\circ\text{F}$) of the targeted value by a suitable automatic device and shall be stated in the report. It is generally recognized that thermal contraction and expansion associated with small temperature changes during the test may produce changes in the apparent creep rate, especially near the transition temperature.

6.6.2 Temperature measurements shall be recorded at frequent intervals, or recorded continuously, in order to ensure an accurate determination of the average test temperature and compliance with [6.6.1](#).

6.7 *Environmental Control and Measurement:*

6.7.1 When the test environment is air, the relative humidity shall be maintained between 50 and 70 % unless the creep or creep rupture behavior of the geosynthetic has been shown to be unaffected by humidity. The relative humidity shall be recorded at frequent intervals to ensure that an accurate determination of the average test humidity can be made.

6.7.2 The test environment shall be maintained constant throughout the test. Safety precautions should be taken to avoid personal contact during the test. The area should be isolated adequately and fenced such that only the test operator has access to the test station.

7. Sampling

7.1 *Laboratory Sample*—For the laboratory sample, take a full-width swatch at least 1 m (40 in.) long in the machine

⁴ Examples of clamping, loading, and extensometer systems that have been used successfully are found in the appendixes.

direction from each roll in the lot sample. The sample may be taken from the end portion of a roll, provided there is no evidence that it is different from other portions of the roll. See Practice D4354.

7.2 Test Specimens:

7.2.1 *Geotextiles and Geomembranes*—For tests in the machine and cross-machine directions, respectively, take from each sample the number of specimens as directed in 9.1. Take the specimens from a diagonal on the sample, with no specimens closer than one tenth the width of the roll or 150 mm (6 in.), whichever is smaller. For geomembranes, exercise care in selecting, cutting, and preparing the specimens to avoid nicks, tears, scratches, folds, or other imperfections that are likely to cause premature failure.

NOTE 1—Nonreinforced geomembranes are extremely sensitive in this regard.

7.2.2 *Geogrids and Other Related Products*—For tests in the machine and cross-machine directions, respectively, take from each sample the number of specimens as directed in 9.1. Take the specimens at random from the laboratory sample. For measurement of machine direction properties, take specimens from different positions across the width of the sample. For the measurement of cross-machine direction properties, take specimens from different positions along the length of the sample. Take no specimens nearer to the edge than one tenth the width of the roll or 150 mm (6 in.), whichever is smaller.

8. Test Specimen

8.1 *Geosynthetics*—Prepare each finished specimen to the width appropriate for the particular geosynthetic with the length dimension parallel to the direction that the creep or creep rupture behavior is being measured.

8.1.1 *Geotextiles*—Cut specimen at least 210 mm (8.4 in.) wide by at least 200 mm (8.0 in.) long. Then strip yarns from each side to leave 200 mm (8.0 in.) width of intact fabric under test.

8.1.2 *Geogrids*—Prepare specimen width to include at least three longitudinal elements abreast parallel to the direction that the creep or creep rupture behavior is being measured with each element long enough to include at least three apertures.

8.1.2.1 *Uniaxial Geogrids*—Cut specimens as illustrated in Fig. 1(a).

8.1.2.2 *Biaxial Geogrids*—Cut ribs around the periphery of a specimen no closer than 10 mm (3/8 in.) to a junction. See Fig. 1(b).

8.2 The length of the specimen depends on the type of clamps being used. The specimen must be long enough to extend through the full length of both clamps, as determined for the direction of the test.

8.3 When specimen integrity is not affected, the specimen may be cut initially to the finished width.

8.4 This test method may not be suitable for some woven geotextiles or geogrids that exhibit breaking strengths in excess of 100 kN/m (570 lbf/in.), due to clamping and equipment limitations.

9. Number of Tests

9.1 Unless otherwise agreed upon, creep and creep rupture tests shall be conducted at load levels as specified by the designer or customer. Four load levels are recommended for characterization of the material. Loads shall be selected at intervals of the maximum load per unit width as determined by the applicable ASTM test methods that are appropriate for the product being tested.

9.1.1 For creep tests, appropriate loads may be between 20 and 80 % of the ultimate tensile strength of the sample being tested, depending on the material being tested.

9.1.2 For creep rupture tests, the loads may be between 30 and 90 % of the ultimate tensile strength of the sample being tested, depending on the material being tested.

NOTE 2—It is generally recognized that characterization involves

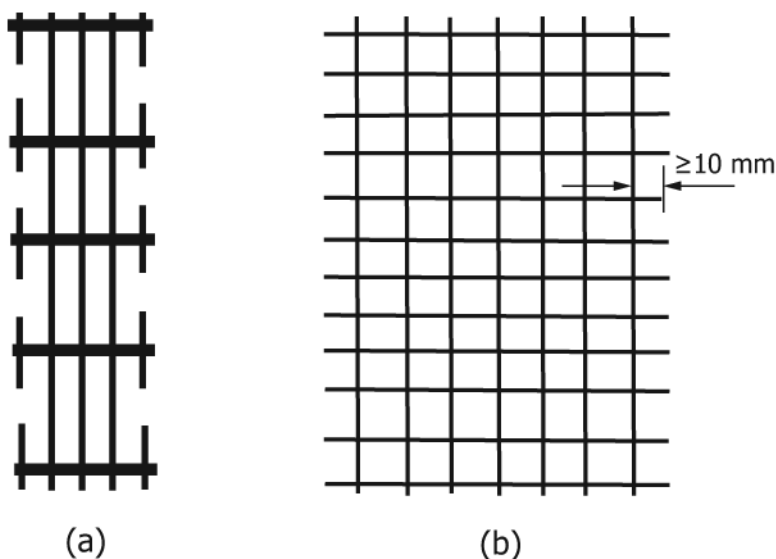


FIG. 1 (a) Uniaxial Geogrid; (b) Biaxial Geogrid