



Designation: D7187 – 20

Standard Test Method for Measuring Mechanistic Aspects of Scratch/Mar Behavior of Paint Coatings by Nanoscratching¹

This standard is issued under the fixed designation D7187; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers a nanoscratch method for determining the resistance of paint coatings on smooth flat surfaces to scratch/mar.

1.2 Other methods used in scratch/mar evaluation physically scratch or mar a sample's surface with single or multiple contact cutting, and then use visual inspection to assign a ranking. It has been recognized that loss of appearance is mainly due to surface damage created. This method quantitatively and objectively measures scratch/mar behavior by making the evaluation process two steps with emphasis on surface damage. Step one is to find the relationship between damage shape and size and external input (such as forces, contact geometry, and deformation). Step two is to relate damage shape and size to visual loss of luster. The first step is covered by this method; in addition, a survey in the appendix provides an example of an experiment to relate the damage to the change in luster.

1.3 There are three elementary deformation mechanisms: elastic deformation, plastic deformation and fracture; only the latter two contribute significantly to mar. This method evaluates scratch/mar based on the latter two damage mechanisms.

1.4 Although this standard was developed for paint coatings, it can also be applied to other types of similar polymer-based coatings, for example, lacquers, varnishes, glazes and other decorative and protective layers deposited on hard substrates.

1.5 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

¹ This test method is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.23 on Physical Properties of Applied Paint Films.

Current edition approved June 1, 2020. Published June 2020. Originally approved in 2005. Last previous edition approved in 2015 as D7187 – 15. DOI: 10.1520/D7187-20.

1.7 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 ASTM Standards:²

- D609 Practice for Preparation of Cold-Rolled Steel Panels for Testing Paint, Varnish, Conversion Coatings, and Related Coating Products
- D823 Practices for Producing Films of Uniform Thickness of Paint, Coatings and Related Products on Test Panels
- D1005 Test Method for Measurement of Dry-Film Thickness of Organic Coatings Using Micrometers
- D1044 Test Method for Resistance of Transparent Plastics to Surface Abrasion by the Taber Abraser
- D3363 Test Method for Film Hardness by Pencil Test (Withdrawn 2020)³
- D3924 Specification for Standard Environment for Conditioning and Testing Paint, Varnish, Lacquer, and Related Materials
- D5178 Test Method for Mar Resistance of Organic Coatings
- D6037 Test Methods for Dry Abrasion Mar Resistance of High Gloss Coatings
- D6279 Test Method for Rub Abrasion Mar Resistance of High Gloss Coatings
- D7027 Test Method for Evaluation of Scratch Resistance of Polymeric Coatings and Plastics Using an Instrumented Scratch Machine
- D7091 Practice for Nondestructive Measurement of Dry Film Thickness of Nonmagnetic Coatings Applied to Ferrous Metals and Nonmagnetic, Nonconductive Coatings Applied to Non-Ferrous Metals
- G171 Test Method for Scratch Hardness of Materials Using a Diamond Stylus

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *ASTM Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

3. Summary of Test Method

3.1 This test method is based on representative samples of the paint film being scratched using a nanoscratch instrument. From information generated during a scratch test, values for plastic resistance (PR) and fracture resistance (FR) can be determined. From these values, the mechanistic aspects of scratch/mar behavior of the coating can be compared.

4. Significance and Use

4.1 This test addresses two limitations in existing mar tests such as Test Methods **D1044**, **D3363**, **D5178**, **D6037**, and **D6279**, namely:

4.1.1 Measured damage is caused by hundreds of contacts with differing contact geometries making it difficult or impossible for mechanical quantities (force, displacement) at the contact points to be reliably determined.

4.1.2 The damage is evaluated using subjective visual assessments, which provide only a qualitative sense of wear with little information about mar mechanisms.

4.2 This test provides a quantitative assessment of a paint coating's mechanistic aspects of scratch/mar behavior in various conditions. The ability to control testing variables such as loading rate, speed, and temperature allow the study of the scratch/mar behavior in a variety of environments.

4.3 This test method is particularly suitable for measurement of paint coatings on laboratory test panels.

4.4 The accuracy and precision of scratch/mar performance may be significantly influenced by coating surface non-uniformity and irregularities.

4.5 A correlation has been observed between good mar resistance in field studies and a combination of high plastic resistance and high fracture resistance. When coatings have had either high plastic resistance and low fracture resistance, or low plastic resistance and high fracture resistance, there have been contradictory results in field studies.

4.6 Mar resistance characterizes the ability of the coating to resist light damage. The difference between mar and scratch resistance is that mar is related to only the relatively fine surface scratches which spoil the appearance of the coating. The mechanistic aspects of mar resistance depend on a complex interplay between visco-elastic and thermal recovery, yield or plastic flow, and micro-fracture. Polymers are challenging because they exhibit a range of mechanical properties from near liquid through rubber materials to brittle solids. The mechanical properties are rate and temperature dependent and visco-elastic recovery can cause scratches to change with time. One such test for evaluating polymeric coatings and plastics is Test Method **D7027**.

4.7 Since this method measures mechanical qualities, such as forces and displacements (deformations) during the damage making process, rate dependence, temperature dependence, and visco-elastic-plastic recovery can be further investigated and visual impacts of damage can be related to deformation mechanisms.

5. Apparatus

5.1 *Paint Application Equipment*, as described in Practices **D609** and **D823**.

5.2 *Nanoscratch Instrument*, consisting of an instrument with a well-defined indenter, which translates perpendicular to the coating surface and has the capacity to produce an instrumented scratch of controlled and variable normal force and continuously measured displacement during testing. The normal force shall be feedback controlled, in order to quickly respond to variations in surface morphology. The force of the instrument should have a maximum normal force of at least $50 \text{ mN} \pm 0.1 \text{ mN}$. The maximum tangential force, if measured, should be at least $50 \text{ mN} \pm 0.5 \text{ mN}$. The range of the displacement sensors should be at least $200 \text{ }\mu\text{m}$ with a resolution of at least 20 nm . Displacement and tangential force response of the coating should be measured with a high data acquisition rate, such as a maximum of $5 \text{ }\mu\text{m}$ between data points.

5.3 *Suggested Range for Testing Parameters:*

5.3.1 Indenter size should range from $1 \text{ }\mu\text{m}$ to $100 \text{ }\mu\text{m}$ and should be spherical in geometry. Indenter material should be diamond.

5.3.2 The scratch should be applied at a rate of 0.5 mm to 10 mm per minute.

5.3.3 The loading rate of the normal force should be applied at 5 mN to 200 mN per minute.

5.3.4 The scanning preload should be conducted with an applied force of 0.1 mN to 1 mN .

5.4 The following is an example of one particular application of the test ranges. This example is based on automotive clear coats on a metal substrate.

5.4.1 Indenter size of $2 \text{ }\mu\text{m}$.

5.4.2 Scratch speed of 3 mm per minute.

5.4.3 Loading rate of 40 mN per minute.

5.4.4 Scanning preload of 0.2 mN .

5.4.5 Data acquisition rate of $3 \text{ }\mu\text{m}$ between data points.

NOTE 1—To optimize test parameters for a particular coating, experiments may need to be conducted as different combinations of applied load and indenter radius will cause differing damage in coatings. A smaller indenter radius (sharper tip) will tend to cut the coating and apply a higher contact pressure, whereas a larger indenter radius (blunter tip) will tend to tear the coating and apply a lower contact pressure.

6. Test Specimen

6.1 The substrate for the paint coating should be a smooth, plane, rigid surface, such as those specified in Practices **D609** and **D823**.

6.2 The thickness of the coating being tested, determined in accordance with either Test Methods **D1005** or **D7091**, should be uniform within 5% of coating thickness.

6.3 At least three scratches shall be performed on each test specimen.

6.4 The surface of the specimens shall be free of any dirt and oils. Care should be taken when cleaning samples: solvents should not be used as they may modify the surface properties

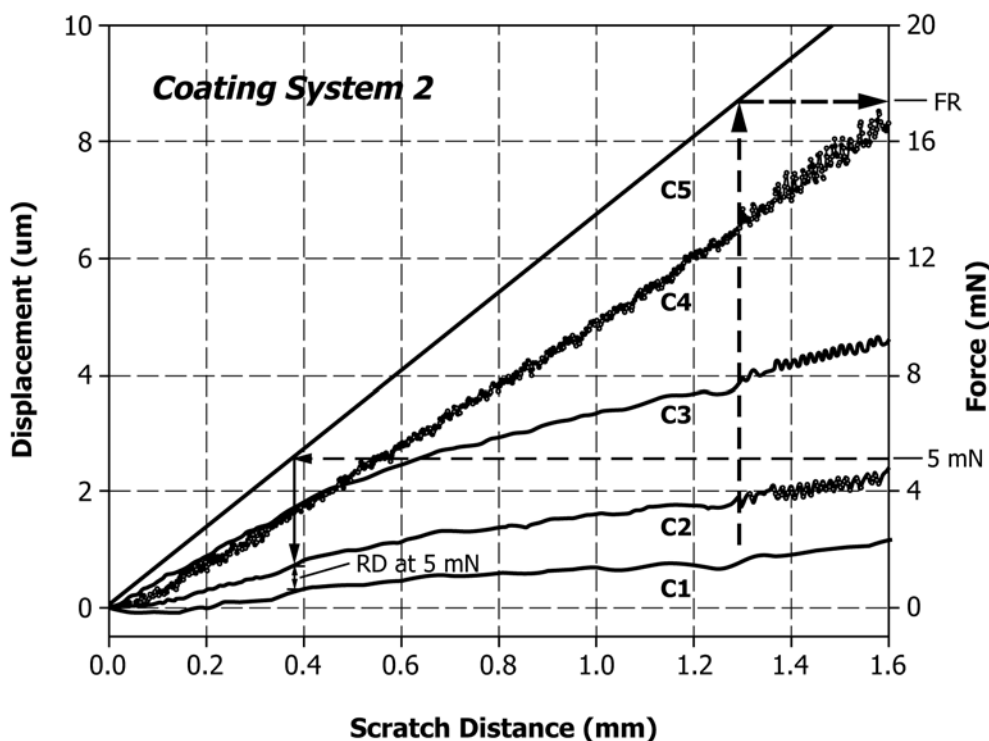


FIG. 1 Example - Typical Data from a Nanoscratch Test (1)

of polymer-based coatings. For removing dust, it is recommended to blow off particulates with compressed air from a clean source (without oil contamination).

6.5 The specimen size should be sufficient to be adequately secured to the nanoscratch instrument, but not so small as to interfere with the movement of the indenter tip or its supporting cantilever.

NOTE 2—It is recommended that substrates with similar compliances be used when comparing different coatings.

7. Conditioning

7.1 Cure the coated test specimens under conditions agreed upon between the purchaser and seller that reflect the conditions of curing of the paint in actual service.

7.2 Condition and test the test specimens at $23\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ ($73.5\text{ }^{\circ}\text{F} \pm 3.5\text{ }^{\circ}\text{F}$) and a relative humidity of $50\% \pm 5\%$ for at least 24 h, unless the purchaser and seller agree on more suitable test characteristics, as specified in the Standard Atmosphere of Specification D3924.

8. Procedure

8.1 Secure the specimen to the moveable stage on the instrument with the surface to be measured located perpendicularly to the indenter tip. Ensure the panel is held rigidly to the stage and cannot be moved by the action of the subsequent scratch test.

8.2 Carefully move this area under the indenter and bring the indenter tip close to the sample surface.

8.3 The complete scratch test consists of three distinct steps. In all three steps, the indenter follows the exact same path across the sample surface.

NOTE 3—A set of sample test parameters can be found in 5.4.

8.3.1 Perform a prescan to measure the topography of the undamaged coating. Apply the lowest load that the instrument can apply but that makes no permanent damage. The prescan, scratch, and postscan must be performed on the same line.

8.3.2 Instruct the instrument to begin making a scratch to produce damage to the coating. Allow the instrument to ramp to the desired normal force at a controlled rate. At the end of the scratch, return the indenter tip to its starting position at the beginning of the scratch.

8.3.3 Without delay perform a postscan, where the indenter tip is scanned along the scratch, measuring the residual topography of the damaged area. This should be done with the lowest load the instrument can apply.

NOTE 4—Prescan and postscan should only be used if the instrument has force feedback control, otherwise significant error may be incurred.

NOTE 5—The prescan and postscan need to be conducted consistently (with the same scanning parameters) before and after the scratch load is applied. This is done to accurately measure recovery aspects since these aspects will vary with time.

8.4 The complete scratch test shall be repeated two more times at different locations so that there are a total of three scratches per test panel.

8.5 Results of typical data from a nanoscratch test are presented in Fig. 1⁴. The graph consists of five curves labeled C₁ through C₅. If required, correct the data by curve fitting so that zero indenter penetration and residual depth (RD) corresponds to zero applied normal force.

⁴ The boldface numbers in parentheses refer to the list of references at the end of this test method.