



Standard Test Methods for Polyurethane Raw Materials: Determination of the Isomer Content of Toluenediisocyanate¹

This standard is issued under the fixed designation D4660; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 These test methods measure the amount of toluene-2,6-diisocyanate (2,6-TDI) isomer or toluene-2,4-diisocyanate (2,4-TDI) isomer in mixtures of the 2,4- and 2,6-isomers of toluenediisocyanate (TDI). Two different test methods are provided to give accurate results over the broad range of isomer concentrations possible.

1.1.1 *Test Method A*—Applicable to TDI samples containing 5 to 95 % of 2,6-TDI isomer (5 to 95 % 2,4-TDI isomer).

1.1.2 *Test Method B*—Applicable to TDI samples containing 0 to 5 % of 2,6-TDI isomer (95 to 100 % 2,4-TDI isomer).

NOTE 1—These test methods are equivalent to ISO 15064.

1.2 The values stated in SI units are to be regarded as standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards*:²

[D883 Terminology Relating to Plastics](#)

[E180 Practice for Determining the Precision of ASTM Methods for Analysis and Testing of Industrial and Specialty Chemicals](#) (Withdrawn 2009)³

2.2 *ISO Standard*:⁴

[ISO 15064 Plastics—Aromatic Isocyanates for Use in the Production of Polyurethanes—Determination of the Iso-](#)

[mer Ratio in Toluenediisocyanate](#)

3. Terminology

3.1 Terminology in these test methods is in accordance with Terminology [D883](#).

3.2 *Definitions of Terms Specific to This Standard*:

3.2.1 *isomer*—a compound having the same molecular formula (percentage composition and molecular weight) as another compound but differs in chemical or physical properties.

3.2.2 *isomer content*—the amount of an isomer expressed as a percentage of total 2,4 and 2,6-TDI isomer amount.

4. Summary of Test Methods

4.1 Both test methods are based on the quantitative measurement of absorption bands arising from out-of-plane C-H deformation vibrations of the aromatic ring.

4.2 In Test Method A, the infrared spectrum of a cyclohexane solution of the sample is recorded in the 770 to 840-cm⁻¹ region. The absorbance ratio of the 805 cm⁻¹ to the 782 cm⁻¹ band is measured and converted to percent 2,6-TDI, or percent 2,4-TDI, or both, from a previously established calibration curve.

4.3 In Test Method B, the absorbance of the 782-cm⁻¹ band is measured from an infrared spectrum of an undiluted sample and then converted to percent 2,6-TDI from a previously established calibration curve.

5. Significance and Use

5.1 These test methods can be used for research or for quality control to determine the isomer content of toluene diisocyanates.

5.2 The isomer content of a toluene diisocyanate relates to its reactivity.

6. Apparatus

6.1 *Spectrophotometer*—Any single- or double-beam recording infrared spectrophotometer accurate to 0.2 % transmission and capable of resolving the two peaks of the 2,4-TDI isomer doublet at 805-815 cm⁻¹ (see [Fig. 1](#)).

6.2 *Cells*, sealed sodium chloride (NaCl) liquid absorption cells with 0.2-mm (Test Method A) and 0.1-mm (Test Method

¹ These test methods are under the jurisdiction of ASTM Committee D20 on Plastics and are the direct responsibility of Subcommittee D20.22 on Cellular Materials - Plastics and Elastomers.

Current edition approved May 1, 2012. Published June 2012. Originally approved in 1959. Last previous edition approved in 2006 as D4660 - 06. DOI: 10.1520/D4660-12.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ The last approved version of this historical standard is referenced on www.astm.org.

⁴ Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036, <http://www.ansi.org>.

*A Summary of Changes section appears at the end of this standard

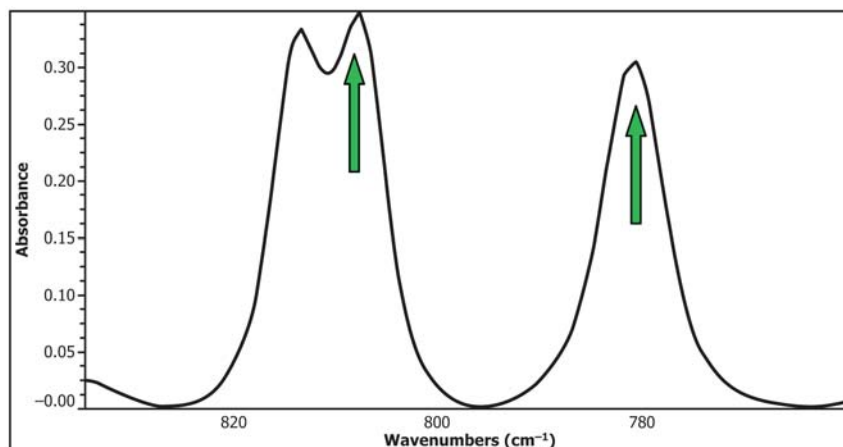


FIG. 1 IR Scan of TDI Showing 2,4-TDI Isomer Doublet at 810 cm^{-1} and 2,6 TDI Isomer at 782 cm^{-1}

B) path lengths. The actual thicknesses of the cells are to be known to ± 0.002 mm.

6.3 *Glassware*, 25-mL, glass-stoppered, volumetric flasks, 10-mL, glass-stoppered, flasks, 0.80-mL volumetric pipet, and an all-glass syringe.

7. Reagents and Materials

7.1 *Purity of Reagents*—Use reagent grade chemicals in all tests. Unless otherwise noted, all reagents conform to the specifications of the Committee on Analytical Reagents of the American Chemical Society where such specifications are available.⁵ Other grades may be used, provided it is ascertained that the reagent is of sufficiently high purity to permit its use without lessening the accuracy of the determination.

7.2 *Cyclohexane*, anhydrous, stored over molecular sieve.

7.3 *Diisocyanate Standards*—Pure samples of 2,4-TDI and 2,6-TDI are required for calibration. The following criteria can be used to judge purity:

Pure Isomer	Freezing point	Refractive Index @ 20C n^{20}_D	Density @ 20C/4C
2,4-TDI	22.0°C	1.56781	1.2186
2,6-TDI	18.2°C	1.57111	1.2270

8. Sampling

8.1 Since organic isocyanates react with atmospheric moisture, take special precautions in sampling. Usual sampling methods, even when conducted rapidly, can cause contamination of the sample with insoluble urea. Therefore, blanket the sample with dry air or nitrogen at all times. (**Warning**—Many diisocyanates are known or suspected sensitizers. Over-exposure to diisocyanates can lead to adverse health effects which include the development of occupational asthma and other respiratory, skin and eye effects. Engineering controls and/or personal protective equipment, including respiratory,

⁵ *Reagent Chemicals, American Chemical Society Specifications*, American Chemical Society, Washington, DC. For suggestions on the testing of reagents not listed by the American Chemical Society, see *Analar Standards for Laboratory Chemicals*, BDH Ltd., Poole, Dorset, U.K., and the *United States Pharmacopeia and National Formulary*, U.S. Pharmacopeial Convention, Inc. (USPC), Rockville, MD.

skin and eye protection, are to be used when there is a potential for over-exposure to diisocyanates. The product suppliers' Material Safety Data Sheet (MSDS) provides more detailed information about potential adverse health effects and other important safety and handling information. Always follow the specific instructions provided on the MSDS.)

9. Test Conditions

9.1 Since isocyanates react with moisture, keep laboratory humidity low, preferably around 50 % relative humidity.

TEST METHOD A—SAMPLES CONTAINING 5 TO 95 % 2,6-TDI

10. Calibration

10.1 Weigh amounts of pure 2,4-TDI and 2,6-TDI into dry, 10-mL, glass-stoppered flasks (**Note 2**) to obtain the weight ratios given in 10.1.1 or 10.1.2. Carefully shake the mixtures. From the weights of pure 2,4-TDI and 2,6-TDI, calculate the weight ratios (2,4-TDI to 2,6-TDI), or the weight percent composition of the mixtures, or both, expressed to four significant figures.

NOTE 2—Carefully dry all glassware since the diisocyanates react readily with moisture.

10.1.1 Approximate standard mixtures for wide-range calibration are given in **Table 1** (5-95 % 2,6-TDI).

TABLE 1 Approximate Standard Mixtures for Wide-Range Calibration, 5–95 % 2,6-TDI

Weight Ratio		
%, 2,4-TDI	%, 2,6-TDI	2,4-/2,6-TDI
5.0	95.0	0.05
10.0	90.0	0.11
20.0	80.0	0.25
30.0	70.0	0.43
40.0	60.0	0.67
50.0	50.0	1.00
60.0	40.0	1.50
70.0	30.0	2.33
80.0	20.0	4.00
90.0	10.0	9.00
95.0	5.0	19.00