



Standard Test Method for Oxidation Stability of Lubricants by Thin-Film Oxygen Uptake (TFOUT) Catalyst B^{1,2}

This standard is issued under the fixed designation D7098; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the oxidation stability of lubricants by thin-film oxygen uptake (TFOUT) Catalyst B. This test method evaluates the oxidation stability of petroleum products, and it was originally developed as a screening test to indicate whether a given re-refined base stock could be formulated for use as automotive engine oil³ (see Test Method D4742). The test is run at 160 °C in a pressure vessel under oxygen pressure, and the sample contains a metal catalyst package, a fuel catalyst, and water to partially simulate oil conditions in an operating engine. In addition, the test method has since been found broadly useful as an oxidation test of petroleum products.⁴

1.2 The applicable range of the induction time is from a few minutes up to several hundred minutes or more. However, the range of induction times used for developing the precision statements in this test method was from 40 min to 280 min.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.3.1 *Exception*—Pressure units are provided in psig, and dimensions are provided in inches in [Annex A1](#) and [Annex A2](#), because these are the industry accepted standard and the apparatus is built according to the figures shown.

¹ This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee D02.09.0G on Oxidation Testing of Engine Oils.

Current edition approved Oct. 1, 2015. Published December 2015. Originally approved in 2005. Last previous edition approved in 2008 as D7098 – 08^{ε1}. DOI: 10.1520/D7098-08R15.

² While Catalyst B can be used for testing oxidation stability of many lubricant types, the mixture of fuel, nitro-paraffin, and catalyst components used in this test method simulates the Sequence IIIE Engine Test. Test results on several ASTM reference oils have been found to correlate with Sequence IIIE engine tests in hours for a 375 % viscosity increase. (See Ku, Chia-Soon, Pei, Patrick T., and Hsu, Stephen M., “A Modified Thin-Film Oxygen Uptake Test (TFOUT) for the Evaluation of Lubricant Stability in ASTM Sequence IIIE Test, SAE Technical Paper Series 902121, Tulsa, OK, Oct. 22-25, 1990.)

³ Ku, C. S. and Hsu, S. M., “A Thin Film Uptake Test for the Evaluation of Automotive Lubricants,” *Lubrication Engineering*, 40, 2, 1984, pp. 75–83.

⁴ Selby, Theodore W., “Oxidation Studies with a Modified Thin-Film Oxygen Uptake Test”, *SAE Technical Paper Series* 872127, Toronto, Ontario, Nov. 2-5, 1987.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:⁵

- A314 Specification for Stainless Steel Billets and Bars for Forging
- B211 Specification for Aluminum and Aluminum-Alloy Rolled or Cold Finished Bar, Rod, and Wire
- D664 Test Method for Acid Number of Petroleum Products by Potentiometric Titration
- D1193 Specification for Reagent Water
- D2272 Test Method for Oxidation Stability of Steam Turbine Oils by Rotating Pressure Vessel
- D4742 Test Method for Oxidation Stability of Gasoline Automotive Engine Oils by Thin-Film Oxygen Uptake (TFOUT)
- E1 Specification for ASTM Liquid-in-Glass Thermometers
- E144 Practice for Safe Use of Oxygen Combustion Vessels

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *break point*—the precise point of time at which rapid oxidation of the oil begins.

3.1.2 *oxidation induction time*—the time until the oil begins to oxidize at a relatively rapid rate as indicated by the decrease of oxygen pressure.

3.1.3 *oxygen uptake*—oxygen absorbed by oil as a result of oil oxidation.

4. Summary of Test Method

4.1 The test oil is mixed in a glass container with four other liquids used to simulate engine conditions: (1) an oxidized/nitrated fuel component ([Annex A3](#)), (2) a mixture of soluble

⁵ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

INDUCTION TIME DETERMINATION

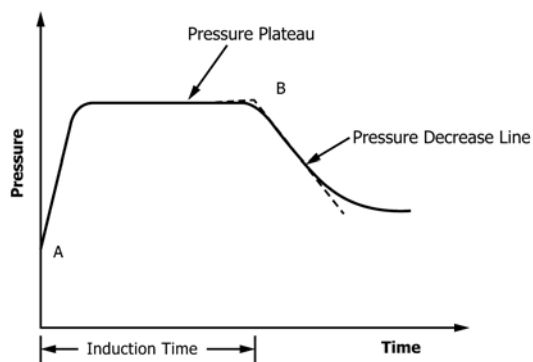


FIG. 1 Pressure versus Time Diagram of the Oxidation Test

metal naphthenates (lead, iron, manganese, and tin naphthenates (Annex A4), (3) a nitro-paraffinic compound, and (4) Type I reagent water.

4.2 The glass container holding the oil mixture is placed in a pressure vessel equipped with a pressure sensor. The pressure vessel is sealed, charged with oxygen to a pressure of 620 kPa (90 psig), and placed in an oil bath at 160 °C at an angle of 30° from the horizontal. The pressure vessel is rotated axially at a speed of 100 r/min forming a thin film of oil within the glass container resulting in a relatively large oil-oxygen contact area.

4.3 The pressure of the pressure vessel is recorded continuously from the beginning of the test and the test is terminated when a rapid decrease of the pressure vessel pressure is observed (Point B, Fig. 1). The period of time that elapses between the time when the pressure vessel is placed in the oil bath and the time at which the pressure begins to decrease rapidly is called the oxidation induction time and is used as a measure of the relative oil oxidation stability.

5. Significance and Use

5.1 This test method was originally developed to evaluate oxidation stability of lubricating base oils combined with additives chemistries similar to those found in gasoline engine oils and service.²

5.2 This test method is useful for screening formulated oils before engine tests. Within similar additive chemistries and base oil types, the ranking of oils in this test appears to be predictive of ranking in certain engine tests. When oils having different additive chemistries or base oil type are compared, results may or may not reflect results in engine tests. Only gasoline engine oils were used in generating the precision statements in this test method.

6. Apparatus

6.1 *Oxidation Bath and Pressure Vessel*—See appropriate Annex (Annex A1⁶ or Annex A2⁷) for detailed description of apparatus and accessories for equipment described in this test method.

NOTE 1—To reduce vapor odors when opening pressure vessel after use, a hood may be desirable.

6.2 *Precision Pressure Gauge*—Use a certified precision pressure gauge to accurately control the oxygen feed to the pressure vessel. The gauge shall have a sufficient range to encompass 0 kPa to 650 kPa (~90 psig) required by the test method with division 2.0 kPa (~0.5 psig) or better to enable readings to be made to 2.0 kPa (~0.25 psig).

7. Reagents

7.1 *Purity of Reagents*—Reagent grade chemicals shall be used in all tests. Unless otherwise indicated, it is intended that all reagents shall conform to the specifications of the Committee on Analytical Reagents of the American Chemical Society.⁸

7.2 *Purity of Water*—Unless otherwise indicated, references to reagent water shall be understood to mean distilled water meeting requirements of reagent water as defined by Type I of Specification D1193.

7.3 *Acetone*, CH₃COCH₃.

7.4 *Air*, containing 2000 ppm nitrogen dioxide, NO₂ (commercially available compressed gas mixture, certified within ±5 %).

7.5 *Cyclo-hexane*, C₆H₁₂, Practical Grade or other suitable hydrocarbon solvent. (**Warning**—Highly flammable. Skin irritant on repeated contact. Aspiration hazard.)

7.6 *Isopropyl Alcohol*, CH₃CH(CH₃)OH.

7.7 *Oxygen*, 99.8 %.

8. Materials

8.1 *TFOUT Catalyst B Package*:⁷

⁶ The sole source of supply of the apparatus known to the committee at this time is Koehler Instrument Co., Inc., 1595 Sycamore Ave., Bohemia, NY11716 and Stanhope-Seta, London St., Chertsey, Surrey, KT16 8AP, U.K. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,¹ which you may attend.

⁷ The sole source of supply of the apparatus known to the committee at this time is Tannas Co., 4800 James Savage Rd., Midland, MI 48642. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,¹ which you may attend.

⁸ *Reagent Chemicals, American Chemical Society Specifications*, American Chemical Society, Washington, DC. For Suggestions on the testing of reagents not listed by the American Chemical Society, see *Annual Standards for Laboratory Chemicals*, BDH Ltd., Poole, Dorset, U.K., and the *United States Pharmacopeia and National Formulary*, U.S. Pharmacopeial Convention, Inc. (USPC), Rockville, MD.

8.1.1 *Fuel Component*—The fuel component is a nitrated gasoline fraction or organic equivalent. This component may be prepared in accordance with the procedures described in [Annex A3](#).

8.1.2 *Soluble Metal Catalyst Mixture*—This catalyst is a mixture of soluble metal catalysts (lead, iron, manganese, and tin). The catalyst may be prepared according to the procedures described in [Annex A4](#).

8.1.2.1 Other oxidation stability test methods have demonstrated that soluble metal catalyst supplies may be inconsistent and have significant effects on the test results. Thus, for test comparisons, the same source and same batch of metal naphthenates shall be used.

NOTE 2—It is good research practice to use the same batches of catalyst components when closely comparing engine oils.

NOTE 3—Slow, steady reactivity of some of the catalyst chemicals can be a problem. Such problems can be reduced by storing the closed catalyst vials in a refrigerator at approximately 5 °C. The catalyst chemicals remain effective up to six months after the septum is punctured, if they are stored as noted above.

8.1.3 *Nitro-paraffin*—This compound is made up of a nitri-alkane blend.

NOTE 4—Suitably prepared catalyst packages may be purchased from Tannas Co.⁷

8.2 *Varnish and Deposit Remover*, water-soluble varnish remover or other engine varnish/deposit removers.

8.3 *Silicone Stopcock Grease*.

9. Preparation of Apparatus

9.1 *Glass Sample Container*—A clean glass sample container is important for obtaining repeatable results. Thorough cleaning can be accomplished by (a) rinsing with cyclo-hexane or other suitable hydrocarbon solvent, (b) soaking in concentrated solution of a water-soluble varnish remover, (c) thoroughly rinsing with water, (d) rinsing with acetone, (e) and permitting to dry.

NOTE 5—A segmented glass reaction dish has been found suitable to prevent premature mixing of the catalyst components (see [Fig. A2.4](#))

9.2 *Cleaning of Pressure Vessel*—Fill with concentrated solution of a water-soluble varnish remover and soak for suitable time, rinse with water, rinse with acetone, and permit to dry.

9.3 *Cleaning of Pressure Vessel Stem*—Periodically disassemble, inspect, and clean the pressure vessel stem. Rinse the inside of the stem with isopropyl alcohol and blow dry with oil free compressed air. For users of apparatus described in [Annex A1](#), periodically insert a dry pipe cleaner into the transducer line opening for removal of potential residue buildup.

NOTE 6—Replace O-rings when reassembling the pressure transducers.

9.4 Periodically pressure test the pressure vessels at 690 kPa (~100 psi) with air or oxygen. If the pressure drops more than 0.690 kPa (~0.1 psi) on the pressure gauge within 60 s, replace the O-ring seals and inspect the valve seals according to manufacturer's directions. If the problem continues, contact the specific equipment manufacturer.

NOTE 7—Previous versions of this test method have called for hydrostatic testing of the pressure vessel. This was found unnecessary at the

relatively low pressures involved in running this test method.

9.5 *Cleaning of Catalyst Syringes*—Use individual catalyst syringes for each catalyst component. Thoroughly clean and dry syringes prior to each use. (See [Annex A5](#) for recommended procedure.)

10. Procedure

10.1 *Weighing and Mixing Sample and Catalyst Components*:

10.1.1 Place the clean glass sample container onto the precision balance and tare.

10.1.2 Weigh 1.500 g \pm 0.001 g of oil sample into the container and tare.

10.1.3 Add 0.045 g \pm 0.001 g of the soluble metal catalyst mixture into the glass sample container and tare.

10.1.4 Add 0.030 g \pm 0.001 g each of the fuel component, nitro-paraffin and reagent water to the glass sample container and tare each time. It is easiest to add the distilled water last and place on top of the oil sample.

10.1.5 Just prior to inserting the glass sample container into the pressure vessel, thoroughly mix the catalyst components within the sample container by hand-rotation (approximately five rotations) and proceed immediately to [10.2](#). Delay may result in variation of results.

10.2 *Pressure Vessel Assembly and Charging*—Immediately and rapidly assemble and charge the pressure vessel in accordance with apparatus type (see [A1.2](#) or [A2.7](#)).

NOTE 8—Avoid releasing the oxygen too rapidly by decreasing the pressure to atmospheric in no less than 1 min to avoid possible foaming and overflow of the sample from the glass sample container.

10.3 *Oxidation*—Before starting the test, bring the heating bath to the test temperature at 160 °C and insert the pressure vessel(s) in accordance with apparatus type (see [A1.3](#) or [A2.8](#)).

10.3.1 Allow the bath temperature to level out at the test temperature, which must occur within 15 min after insertion of the pressure vessel. Maintaining the test temperature within the specified limits of 160 °C \pm 0.3 °C during the entire test run is the most important single factor ensuring both repeatability and reproducibility of test results. If the test temperature cannot be maintained as specified, the test results shall not be considered valid.

NOTE 9—The time for the bath to reach the operating temperature after insertion of the pressure vessel may differ for different apparatus assemblies and shall be observed for each unit (a unit may carry one, two, three, or four pressure vessels). The objective is to find a set of conditions, which does not permit a drop of more than 2 °C after insertion of the pressure vessel(s) and allows the pressure vessel pressure to reach plateau within 15 min.

10.4 Keep the pressure vessel completely submerged and maintain continuous and uniform rotation throughout the test. A standard rotational speed of 100 r/min \pm 5 r/min is required; any variation in this speed could cause erratic results.

10.5 Monitor the pressure of the pressure vessel preferably using a strip chart or some other form of electronic data collection program. If a dial pressure gauge is used, make readings at least every 5 min. (The maximum pressure must be