



# Standard Test Method for Tensile Strain-Hardening Exponents (*n* -Values) of Metallic Sheet Materials<sup>1</sup>

This standard is issued under the fixed designation E646; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## INTRODUCTION

This test method for determining tensile strain-hardening exponents *n* utilizes stress-strain data obtained in a uniaxial tension test. Tensile data are obtained in a continuous and rate-controlled manner via displacement or strain control. The strain-hardening exponents are determined from an empirical representation over the range of interest of the true-stress versus true-strain curve. The mathematical representation used in this method is a power curve (Note 1) of the form (1)<sup>2</sup>:

$$\sigma = K\epsilon^n$$

where:

$\sigma$  = true stress,

$\epsilon$  = plastic component of true strain, but in special cases may be the total true strain. (See 10.2),

K = is a constant, often called the strength coefficient having the units of stress, and

n = strain-hardening exponent

## 1. Scope\*

1.1 This test method covers the determination of a strain-hardening exponent by tension testing of metallic sheet materials for which plastic-flow behavior obeys the power curve given in the Introduction.

NOTE 1—A single power curve may not be a satisfactory fit to the entire stress-strain curve between yield and necking. If such is the case, more than one value of the strain-hardening exponent may be obtained (2) by agreement using this test method.

1.2 This test method is specifically for metallic sheet materials with thicknesses of at least 0.005 in. (0.13 mm) but not greater than 0.25 in. (6.4 mm). The method has successfully been and may be applied to other forms and thicknesses by agreement

1.3 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

NOTE 2—The value of the strain-hardening exponent, *n*, has no units and is independent of the units used in its determination

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>3</sup>

- E4 Practices for Force Verification of Testing Machines
  - E6 Terminology Relating to Methods of Mechanical Testing
  - E8/E8M Test Methods for Tension Testing of Metallic Materials
  - E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications
  - E83 Practice for Verification and Classification of Extensometer Systems
  - E111 Test Method for Young's Modulus, Tangent Modulus, and Chord Modulus
  - E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods
  - E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method
- ### 2.2 ISO Standard
- ISO 10275:2007 Metallic materials -- Sheet and strip -- Determination of tensile strain hardening exponent

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee E28 on Mechanical Testing and is the direct responsibility of Subcommittee E28.02 on Ductility and Formability.

Current edition approved Feb. 1, 2016. Published March 2016. Originally approved in 1978. Last previous edition approved in 2015 as E646 - 15. DOI: 10.1520/E0646-16

<sup>2</sup> The boldface numbers in parentheses refer to the list of references appended to this method.

<sup>3</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard

### 3. Terminology

3.1 For definitions of other terms used in this test method, refer to **E6** (Standard Terminology Relating to Methods of Mechanical Testing).

#### 3.2 Definitions:

3.2.1 *elastic true strain,  $\epsilon_e$* ,  $n$ —elastic component of the true strain.

3.2.2 *engineering strain,  $e$* ,  $n$ —a dimensionless value that is the change in length ( $\Delta L$ ) per unit length of original linear dimension ( $L_0$ ) along the loading axis of the specimen; that is,  $e = \Delta L/L_0$ .

3.2.3 *engineering stress,  $S$  [ $FL^{-2}$ ]*,  $n$ —the normal stress, expressed in units of applied force,  $F$  per unit of original cross-sectional area,  $A_0$ ; that is,  $S = F/A_0$

3.2.4 *necking,  $n$* —the onset of nonuniform or localized plastic deformation, resulting in a localized reduction of cross-sectional area.

3.2.5 *plastic true strain,  $\epsilon_p$* ,  $n$ —the inelastic component of true strain.

3.2.6 *strain hardening,  $n$* —an increase in hardness and strength caused by plastic deformation.

3.2.7 *true strain,  $\epsilon$* ,  $n$ —the natural logarithm of the ratio of instantaneous gauge length,  $L$ , to the original gauge length,  $L_0$ ; that is,  $\epsilon = \ln(L/L_0)$  or  $\epsilon = \ln(1+e)$ .

3.2.8 *true stress,  $\sigma$  [ $FL^{-2}$ ]*,  $n$ —the instantaneous normal stress, calculated on the basis of the instantaneous cross-sectional area,  $A$ ; that is,  $\sigma = F/A$ ; if no necking has occurred,  $\sigma = S(1+e)$ .

#### 3.3 Definitions of Terms Specific to This Standard:

3.3.1 *strain-hardening exponent ( $n$ )*,  $n$ —an experimental constant, computed from the least squares best fit, linear slope of  $\log \sigma$  versus  $\log \epsilon$  data over a specific strain range where  $\epsilon$  is the plastic component of true strain, but in special cases may be the total true strain (see **10.2**).

3.3.2 *strength coefficient ( $K$ ) [ $FL^{-2}$ ]*,  $n$ —an experimental constant, computed from the fit of the data to the assumed power curve, that is numerically equal to the extrapolated value of true stress at a true strain of 1.00.

### 4. Summary of Test Method

4.1 This test method applies to materials exhibiting a continuous stress-strain curve in the plastic region. The displacement or strain is applied in a continuous and rate-controlled manner while the normal tensile load and strain are monitored. The instantaneous cross-sectional area may be monitored or calculated by assuming constancy of volume in the plastic region. Equations are presented that permit the calculation of the true stress,  $\sigma$ , true strain,  $\epsilon$ , strain-hardening exponent,  $n$ , and strength coefficient,  $K$ , for that continuous portion of the true-stress versus true-strain curve which follows the empirical relationships described.

NOTE 3—This test method is recommended for use only in the plastic

range for metallic sheet material for which the true-stress true-strain data follow the stated relationship.

### 5. Significance and Use

5.1 This test method is useful for estimating the strain at the onset of necking in a uniaxial tension test (**1**). Practically, it provides an empirical parameter for appraising the relative stretch formability of similar metallic systems. The strain-hardening exponent is also a measure of the increase in strength of a material due to plastic deformation.

5.2 The strain-hardening exponent may be determined over the entire plastic stress-strain curve or any portion(s) of the stress-strain curve specified in a product specification.

NOTE 4—The engineering strain interval 10–20% is commonly used for determining the strain-hardening exponent,  $n$ , of formable low-carbon steel products

5.3 This test method is not intended to apply to any portion of the true stress versus true strain curve that exhibits discontinuous behavior; however, the method may be applied by curve-smoothing techniques as agreed upon.

NOTE 5—For example, those portions of the stress-strain curves for mild steel, aluminum, or other alloys that exhibit yield point and Lüders band elongation, twinning, or Portevin–Le Chatelier effect (PLC) may be characterized as behaving discontinuously.

NOTE 6—Caution should be observed in the use of curve-smoothing techniques as they may affect the  $n$ -value.

5.4 This test method is suitable for determining the tensile stress-strain response of metallic sheet materials in the plastic region prior to the onset of necking.

5.5 The  $n$ -value may vary with the displacement rate or strain rate used, depending on the metal and test temperature.

### 6. Apparatus

6.1 *Testing Machines*—Machines used for tension testing shall conform to the requirements of Practices **E4**. The forces used to determine stress shall be within the force range of the testing machine as defined in Practices **E4**.

6.2 *Strain-Measurement Equipment*—Equipment for measurement of extension shall conform to the requirements of Class C or better as defined in Practice **E83**.

### 7. Sampling

7.1 Samples shall be taken from the material as specified in the applicable product specification.


### 8. Test Specimens

#### 8.1 Selection and Preparation of Specimens:

8.1.1 In the selection of specimen blanks, special care shall be taken to assure obtaining representative material that is flat and uniform in thickness.

8.1.2 In the preparation of specimens, special care shall be taken to prevent the introduction of residual stresses.

8.2 *Dimensions*—Recommended metallic sheet specimen configurations are shown in **Fig. 1**. Specimen configurations shall have sides parallel to 0.001 in. and dimensions shall be reported as stated in **11.1.6**.

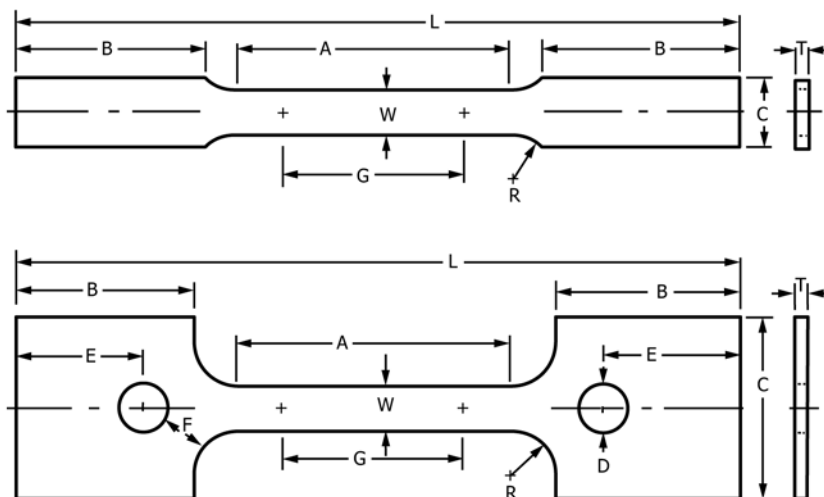

**Dimensions**

Required Dimensions for Reduced Section of Specimen

	Dimensions	
	in.	mm
G Gage length	2.000 ± 0.005	50.0 ± 0.10
W Width <sup>A</sup>	0.500 ± 0.010	12.5 ± 0.25
T Thickness <sup>B</sup>	thickness of material	
R Radius of fillet, min	1/2	13
L Overall length, min	8	200
A Length of reduced section, min	2 1/4	60
B Length of grip section, min	2	50

Suggested Dimensions for Ends of Specimen

"Plain-End" Specimens

C Width of grip section <sup>C and D</sup>	3/4	20
--	-----	----

"Pin-End" Specimens

C Width of grip section, approximate <sup>E</sup>	2	50
D Diameter of hole for pin <sup>F</sup>	1/2	13
E Distance of center of pin from end, approximate	1 1/2	38
F Distance of edge of hole from fillet, min	1/2	13

<sup>A</sup> The width of the reduced section shall be parallel to within ±0.001 in. (±0.025 mm).

<sup>B</sup> The thickness of the reduced section shall not vary by more than ±0.0005 in. (0.013 mm) or 1 %, whichever is larger, within the gage length, G.

<sup>C</sup> It is desirable, if possible, that the grip sections be long enough to extend into the grips a distance equal to two-thirds or more the length of the grips.

<sup>D</sup> Narrower grip sections may be used. If desired, the width may be 0.500±0.010 in. (12.5 ± 0.25 mm) throughout the length of the specimen, but the requirement for dimensional tolerance in the central reduced section stated in footnote A shall apply. The ends of the specimen shall be symmetrical with the center line of the reduced section within 0.01 in. (0.25 mm).

<sup>E</sup> The ends of the specimen shall be symmetrical with the center line of the reduced section within 0.01 in. (0.25 mm).

<sup>F</sup> Holes shall be on the centerline of the reduced section, within ±0.002 in. (±0.05 mm).

**FIG. 1 Specimen for Determining *n*-Values**

NOTE 7—While this standard is specifically for metallic sheet materials, it has been successfully applied to many tensile specimens having a uniform cross-sectional area, for example, round bars and flats where parallel sides have been maintained to within 0.001 in. as required by 8.2. Since other test results may be desired to be obtained, specimens may be intentionally tapered with sides parallel to within the same tolerance of 0.001 in.

**9. Procedure**

9.1 Measure and record the original thickness T, of the reduced section of the specimen to at least the nearest 0.0005 in. (0.013 mm) and the width, W, of the reduced section to at least the nearest 0.001 in. (0.025 mm).

9.1.1 The method to record observed values, given in 7.2 of Practice E29, shall be used for all measurements.

9.2 Grip the specimen in the testing machine in a manner to ensure axial alignment of the specimen as noted in Test Methods E8/E8M and attach the extensometer.

9.2.1 The order of this step may be reversed if required by the design of the extensometer or the specimen grips, or both.

**9.3 Speed of Testing:**

9.3.1 The speed of testing shall be such that the loads and strains are accurately indicated.

9.3.2 In the absence of any specified limitations on the speed of testing (by, for example, the appropriate product specification), the test speed, defined in terms of rate of separation of heads during tests, free running crosshead speed, or rate of straining shall be between 0.05 in./in. (m/m) and 0.50 in./in. (m/m) of the length of the reduced section per minute (in accord with Test Method E8/E8M, Standard Test Methods for Tension Testing Metallic Materials, 7.6.4 Speed of Testing When Determining Tensile Strength) The speed setting shall not be changed during the strain interval over which the strain hardening exponent, *n*, is to be determined