



Designation: B386/B386M – 19^{ε1}

Standard Specification for Molybdenum and Molybdenum Alloy Plate, Sheet, Strip, Foil, and Ribbon¹

This standard is issued under the fixed designation B386/B386M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

^{ε1} NOTE—An editorial correction was made to Table 4 in January 2020.

1. Scope

1.1 This specification covers unalloyed molybdenum and molybdenum alloy plate, sheet, strip, foil, and ribbon as follows:

1.1.1 *Molybdenum 360*—Unalloyed vacuum arc-cast molybdenum.

1.1.2 *Molybdenum 361*—Unalloyed powder metallurgy molybdenum.

1.1.3 *Molybdenum Alloy 363*—Vacuum arc-cast molybdenum-0.5 % titanium-0.1 % zirconium (TZM) alloy.

1.1.4 *Molybdenum Alloy 364*—Powder metallurgy molybdenum-0.5 % titanium-0.1 % zirconium (TZM) alloy.

1.1.5 *Molybdenum 365*—Unalloyed vacuum arc-cast molybdenum, low carbon.

1.1.6 *Molybdenum Alloy 366*—Vacuum arc-cast molybdenum-30 % tungsten alloy.

1.1.7 *Drawing Grade*—A drawing grade is defined, which may be specified as a separate requirement by the purchaser.

1.2 Units—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

1.2.1 The ball punch deformation test called for in 8.4 is a test that is specified in the inch-pound system, and original test results used to produce Fig. 2 were all obtained using inch-pound measurements. For this reason, the graph of minimum required cup height as a function of sheet thickness has been retained in its original inch-pound system. The graphical data has been scanned and a straight line fitted to the scan data. The equation of this line is included in both inch-pound and SI units.

¹ This specification is under the jurisdiction of ASTM Committee B10 on Reactive and Refractory Metals and Alloys and is the direct responsibility of Subcommittee B10.04 on Molybdenum and Tungsten.

Current edition approved Nov. 1, 2019. Published December 2019. Originally approved in 1991. Last previous edition approved in 2011 as B386–03 (2011). DOI: 10.1520/B0386_B0386M-19E01.

1.3 The following precautionary caveat pertains only to the test method portions of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards*:²

E8 Test Methods for Tension Testing of Metallic Materials [Metric] E0008_E0008M

E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

E92 Test Methods for Vickers Hardness and Knoop Hardness of Metallic Materials

E345 Test Methods of Tension Testing of Metallic Foil

E384 Test Method for Microindentation Hardness of Materials

E643 Test Method for Ball Punch Deformation of Metallic Sheet Material

E1941 Test Method for Determination of Carbon in Refractory and Reactive Metals and Their Alloys by Combustion Analysis

3. Terminology

3.1 *Definitions of Terms Specific to This Standard* (Note that definitions reflect varying nomenclature from producer to producer, and are not necessarily exclusive, for example, sheet/ribbon/strip; foil/ribbon/strip):

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

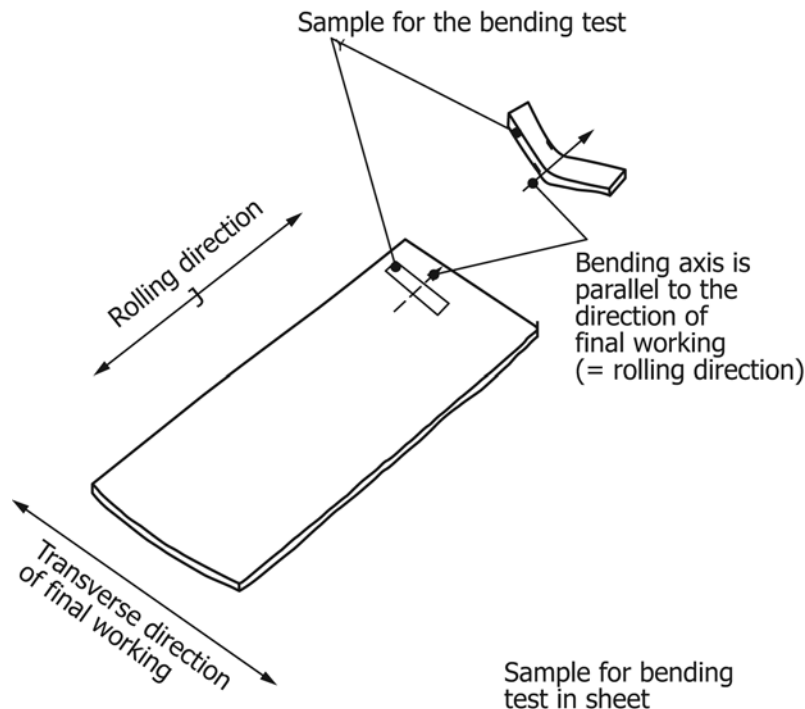


FIG. 1 Sample for Bending Test

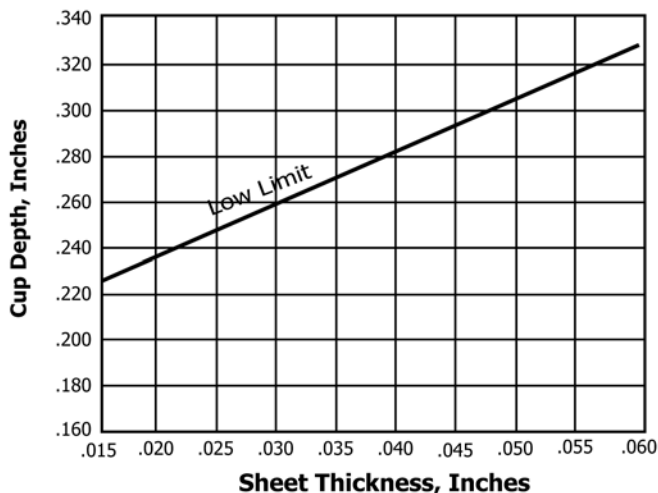


FIG. 2 Ball Punch Deformation Requirements for Drawing Grade Sheet

3.1.1 *drawing grade, n*—sheet having thickness from 0.015 in. [0.38 mm] to 0.060 in. [1.52 mm], intended for applications which require drawability.

3.1.2 *foil, n*—product less than 0.005 in. [0.13 mm] in thickness; foil is typically rolled dominantly in one direction.

3.1.3 *lot, n—for chemical composition*, the ingots obtained from a single blend of powder, sintered together under the same conditions, or the ingots obtained from a single vacuum-melted ingot.

3.1.4 *lot, n—for mechanical property measurement*, the product manufactured from ingots sintered from either a single powder lot in a single sintering run in the same furnace or a

single ingot, processed through the same processing equipment in a single uninterrupted run, using the same thermomechanical process to reach the same final size.

3.1.5 *plate, n*—product 0.187 in. [4.75 mm] or more in thickness. Depending upon starting ingot thickness and finished plate thickness, Plate may be rolled unidirectionally (in a single direction), or cross-rolled (rolled in different directions).

3.1.6 *recrystallized (RX), adj*—the microstructural condition of product annealed after final rolling to obtain an essentially fully recrystallized microstructure consisting of equiaxed or nearly equiaxed grains.

3.1.7 *ribbon, n*—product less than 0.02 in [0.51 mm] in thickness, coiled and mainly rolled unidirectionally.

3.1.8 *sheet, n*—product less than 0.187 in. [4.75 mm] in thickness, to a minimum of 0.005 in. [0.13 mm] in thickness. Sheet is usually rolled mainly in one direction, and depending upon thickness may be produced as individual flat pieces or in coils.

3.1.9 *standard grade, n*—sheet ordered without additional requirements imposed for drawability.

3.1.10 *stress relieved (SR), adj*—the microstructural condition of product annealed after final rolling to improve ductility. This condition may contain a small fraction of recrystallized grains.

3.1.11 *strip, n*—sheet product less than 5 in. [127 mm] in width. Strip may be produced on a mill that rolls to the width specified, or may be cut from wider sheets.

4. Ordering Information

4.1 Orders for material under this specification shall include the following information as applicable: