



Designation: F1336 – 20

Standard Specification for Poly(Vinyl Chloride) (PVC) Gasketed Sewer Fittings¹

This standard is issued under the fixed designation F1336; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reappraisal.

1. Scope*

1.1 This specification covers requirements and test methods for fabricated or molded poly(vinyl chloride) (PVC) gasketed sewer fittings to be used with piping manufactured to Specifications D3034, F679, F891 or F1760. Fabricated fittings may be manufactured from pipe, or from a combination of pipe and injection molded parts, or from injection molded parts. Gasketed sewer fitting configurations may include one or more spigot outlets.

1.2 The requirements of this specification are to provide fabricated or molded PVC gasketed fittings suitable for non-pressure drainage of sewage and surface water, as well as applications involving subsurface drainage.

NOTE 1—Industrial waste lines should be installed only with the specific approval of the governing code authority when using chemicals not commonly found in drains and sewers or temperatures in excess of 140 °F (60 °C), or both.

1.3 Fittings produced to this specification are intended to be installed with pipe, in accordance with Practice D2321.

1.4 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.5 The following precautionary caveat pertains to the test method portion only, Section 10, of this specification. *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This specification is under the jurisdiction of ASTM Committee F17 on Plastic Piping Systems and is the direct responsibility of Subcommittee F17.62 on Sewer.

Current edition approved Nov. 1, 2020. Published December 2020. Originally approved in 1991. Last previous edition approved in 2015 as F1336 – 15. DOI: 10.1520/F1336-20.

2. Referenced Documents

2.1 ASTM Standards:²

- D618 Practice for Conditioning Plastics for Testing
- D1600 Terminology for Abbreviated Terms Relating to Plastics
- D1784 Classification System and Basis for Specification for Rigid Poly(Vinyl Chloride) (PVC) Compounds and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds
- D2122 Test Method for Determining Dimensions of Thermoplastic Pipe and Fittings
- D2321 Practice for Underground Installation of Thermoplastic Pipe for Sewers and Other Gravity-Flow Applications
- D2444 Practice for Determination of the Impact Resistance of Thermoplastic Pipe and Fittings by Means of a Tup (Falling Weight)
- D2564 Specification for Solvent Cements for Poly(Vinyl Chloride) (PVC) Plastic Piping Systems
- D2749 Symbols for Dimensions of Plastic Pipe Fittings
- D3034 Specification for Type PSM Poly(Vinyl Chloride) (PVC) Sewer Pipe and Fittings
- D3212 Specification for Joints for Drain and Sewer Plastic Pipes Using Flexible Elastomeric Seals
- F412 Terminology Relating to Plastic Piping Systems
- F477 Specification for Elastomeric Seals (Gaskets) for Joining Plastic Pipe
- F610/F610M Practice for Evaluating the Quality of Molded Poly(Vinyl Chloride) (PVC) Plastic Pipe Fittings by the Heat Reversion Technique
- F656 Specification for Primers for Use in Solvent Cement Joints of Poly(Vinyl Chloride) (PVC) Plastic Pipe and Fittings
- F679 Specification for Poly(Vinyl Chloride) (PVC) Large-Diameter Plastic Gravity Sewer Pipe and Fittings
- F891 Specification for Coextruded Poly(Vinyl Chloride) (PVC) Plastic Pipe With a Cellular Core
- F913 Specification for Thermoplastic Elastomeric Seals (Gaskets) for Joining Plastic Pipe

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard

F1760 Specification for Coextruded Poly(Vinyl Chloride) (PVC) Non-Pressure Plastic Pipe Having Reprocessed-Recycled Content

2.2 *Federal Standard:*

Fed. Std. No. 123 Marking for Shipment (Civil Agencies)³

2.3 *Military Standard:*

MIL-STD-129 Marking for Shipment and Storage³

3. Terminology

3.1 Definitions are in accordance with Terminology F412 unless otherwise specified.

3.1.1 Abbreviations are in accordance with Terminology D1600, unless otherwise indicated. The abbreviation for poly-(vinyl chloride) plastic is PVC. The abbreviation for plastic sewer main is PSM.

4. Materials and Manufacture

4.1 *Basic Materials*—The pipe components for fabricated fittings shall be made from PVC compounds meeting the cell classifications indicated under the material section of the pipe standards referenced in 1.1. Molded components or fittings shall be made from virgin or rework PVC compound having a cell classification of 12454 or 13343 as prescribed in Specification D1784. Virgin or rework compounds that have different cell classifications because one or more properties exceed the minimum requirements of those specified compounds are also acceptable.

4.2 *Rework Material*—Clean rework material generated from the manufacturer’s own pipe, molded components, or fittings production may be used by the same manufacturer providing the rework material meets the requirements of 4.1

³ DLA Document Services Building 4/D 700 Robbins Avenue Philadelphia, PA 19111-5094 <http://quicksearch.dla.mil/>

and that the pipe, molded components, or fittings produced meet all the requirements of this specification.

5. Miscellaneous Requirements

5.1 *Gasketed Joining System:*

5.1.1 The assembled joint shall display no leakage when tested in accordance with the requirements of Specification D3212.

5.1.2 The joint assembly shall be in accordance with the fitting manufacturer’s recommendations. The end of the pipe or fitting spigot shall not damage or dislodge the gasket during insertion. Lubricant is required on the spigot and sometimes additionally on the gasket. All surfaces of the joint that make contact with the gasket shall be smooth and free of imperfections, ridges, fractures, or cracks that could adversely affect the seal.

5.1.3 The dimensions of the elastomeric gasket seal joints shall accommodate pipes and fitting spigots having the average outside diameters and tolerances detailed in Table 1.

5.2 *Elastomeric Seal Components :*

5.2.1 *Bells*—The dimensions shall be in accordance with the manufacturer’s standard design dimensions and tolerances.

5.2.2 *Gaskets*—The elastomeric seal (gasket) shall comply with the requirements of Specifications F477 or F913 at the time the fittings are manufactured.

5.3 *Lubricant*—The lubricant used for field assembly shall be the type recommended by the manufacturer of the gasketed joint.

5.4 *Fabrication Joint Material*—The fabrication joint material or reinforcing overlays shall be of that type, strength, and properties suitable for the intended fabrication. It is the decision of the manufacturer as to what material will be used.

TABLE 1 Dimensions and Tolerances

Nominal Size in. (mm)	Outside Diameter		Wall Thickness ^A								Wall Thickness in accordance with Specification F679			
	Average		Tolerance		SDR35		SDR26		DR23.5		PS46		PS115	
	in.	mm	in. ±	mm ±	in.	mm	in.	mm	in.	mm	in.	mm	in.	mm
4 (100)	4.215	107.06	±0.009	±0.23	0.120	3.05	0.162	4.11	0.178	4.52
5 (125)	5.640	143.26	±0.010	±0.25	0.161	4.09	0.217	5.51
6 (150)	6.275	159.39	±0.011	±0.28	0.180	4.57	0.241	6.13	0.265	6.73
8 (200)	8.400	213.36	±0.012	±0.30	0.240	6.10	0.323	8.20
10 (250)	10.500	266.70	±0.015	±0.38	0.300	7.62	0.404	10.26
12 (300)	12.500	317.50	±0.018	±0.46	0.360	9.14	0.481	12.22
15 (375)	15.300	388.62	±0.023	±0.58	0.437	11.10	0.588	14.94
18 (450)	18.700	474.98	±0.028	±0.71	0.536	13.61	0.719	18.26	0.499	12.70	0.671	17.00
21 (525)	22.047	559.99	±0.033	±0.84	0.632	16.05	0.848	21.54	0.588	14.90	0.791	20.10
24 (600)	24.803	630.00	±0.037	±0.94	0.711	18.06	0.954	24.23	0.661	15.50	0.889	22.60
27 (675)	27.953	710.01	±0.042	±1.07	0.801	20.35	1.075	27.31	0.745	18.90	1.002	25.50
30 (750)	32.000	813.00	±0.040	±1.02	0.914	23.21	1.231	31.26	0.853	21.70	1.148	29.10
36 (900)	38.300	973.00	±0.050	±1.27	1.094	27.79	1.473	37.42	1.021	25.90	1.373	34.10
42 (1050)	44.500	1130.00	±0.060	±1.52	1.271	32.28	1.740	43.47	1.187	30.10	1.596	40.50
48 (1200)	50.800	1290.00	±0.075	±1.90	1.451	36.86	1.954	49.63	1.355	34.40	1.822	46.30
54 (1350)	57.560	1462.00	±0.085	±2.15	1.535	39.00	2.064	52.40
60 (1500)	61.610	1565.00	±0.090	±2.30	1.643	41.70	2.210	56.10

^A10 % variation resulting from a core shift or other processes is allowable; however, the average of the two opposite wall thickness shall equal or exceed the value shown in the table.

The PVC primer shall meet the requirements of Specification F656. The PVC solvent cement shall meet the requirements of Specification D2564.

5.5 *Over-Wrapped Fittings*—Fabricated fittings that have a reinforcing overlay of fiberglass and thermosetting resin shall meet all of the requirements of this specification except for 4.1 and 4.2.

5.6 *Pipe Performance*—When pipe is used to fabricate a fitting, the pipe shall meet the requirements of the relevant ASTM standards.

5.7 *Waterway*—Fabricated fittings shall be constructed so that pipe ends do not project into the waterway of the fitting body.

6. Dimensions and Permissible Variations

6.1 *Diameter*—The average outside diameter of molded fitting spigots or of spigot pipe components for fabricated fittings shall meet the requirements given in Table 1 when measured in accordance with 10.1.1.

6.2 *Wall Thickness:*

6.2.1 *Fabricated Fittings*—Pipe wall thickness shall meet the requirements of the applicable specifications mentioned in the scope of this specification when measured in accordance with Test Method D2122 and 10.1.2, and shall have a minimum pipe stiffness of 46 psi. In the case of fittings fabricated from pipe sections, the thickness of the wall in the bell and the branch area shall be considered satisfactory if it was formed from pipe meeting those requirements.

6.2.2 *Molded Fittings or Components*—The wall thickness of the waterway and socket or bell of molded fittings or components shall be no less than the respective minimum thickness indicated in Table 1. For reducing fittings or those with smaller inlets, the minimum wall thickness of each inlet shall be no less than the minimum wall thickness indicated in Table 1 for that nominal pipe size. The thickness shall be determined in accordance with Test Method D2122 and 10.1.2

NOTE 2—Refer to Fig. 1, Fig. 2, and Appendix X1 for geometric configurations as illustrations of some of the fittings being produced. Consult the individual manufacturer for laying lengths.

6.3 *Socket Length*—The minimum distance from the center of the gasket to the bottom of the socket and the maximum distance from the center of the gasket to the outermost edge of fitting socket (see Fig. 3) shall comply with the dimensions given in Table 2 when measured in accordance with Test Method D2122 and 10.1.3.

6.4 *Spigot Length*—The minimum distance from the spigot end to the area where spigot diameter changes due to a socket, branch, or change in angle shall comply with the dimensions given in Table 2 when measured in accordance with 10.1.4.

7. Mechanical Properties

7.1 *Impact Strength*—The impact strength of tees, wyes, couplings, bends, increasers/reducers, and saddles shall be no less than the values given in Table 3, when tested in accordance with 10.2.

NOTE 3—This test is intended only for use as a quality control test; not

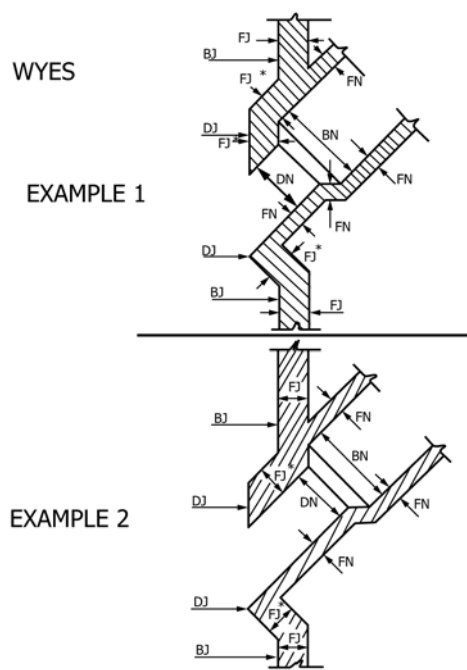


FIG. 1 Product Design Examples

for use as a simulated service test.

7.2 *Pipe Stop Load Support*—Tee, tee-wye, or saddle tee shall support the load indicated in Table 4, when tested in accordance with 10.3.

NOTE 4—This test is intended only for use as a quality control test; not for use as a simulated service test.

7.3 *Internal Stress*—Molded components or fittings shall be tested in accordance with 10.4.

7.4 *Branch Bending*—The wye or tee branch of a fabricated fitting shall be subject to a load in accordance with 10.5.

NOTE 5—This is intended only for use as a quality control test; not for use as a simulated service test.

8. Workmanship, Finish, and Appearance

8.1 The fittings shall be homogeneous throughout and free from visible cracks, holes, foreign inclusions, or other injurious defects. The fittings shall be as uniform as commercially practical in color, opacity, density, and other physical properties.

9. Sampling and Conditioning

9.1 *Sampling*—The selection of fitting samples shall be as agreed upon between the purchaser and the seller. In case of no prior agreement, samples selected by the testing laboratory shall be deemed adequate.

9.2 *Conditioning:*

9.2.1 *Referee Testing*—The specimen shall be conditioned in accordance with Procedure A of Practice D618 at 73 ± 4 °F (23 ± 2 °C) and 50 ± 5 % relative humidity for not less than 40 h prior to test. Tests shall be conducted at the same conditions of temperature and humidity, unless otherwise specified.