



Designation: F2984 – 13 (Reapproved 2019)

Standard Specification for Segmental Panel System for the Grout-in-Place-Liner (GIPL) Rehabilitation Method of Existing Man-Entry Size Sewers, Culverts, and Conduits¹

This standard is issued under the fixed designation F2984; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This specification covers the requirements and test methods for the materials, dimensions, workmanship, and finished quality of injection molded poly vinyl chloride (PVC) profile sections used for the field fabrication of a PVC liner inside existing man-entry size circular and non-circular sewers; circular, non-circular, and box culverts, conduits, and vertical shafts or manholes having dimensions of 39.4 in. and larger (1000 mm and larger).

1.2 The segmental panel system produced under this specification is for non-pressure applications where the PVC liner is installed in the existing structure and the annular space between the liner and the existing structure is grouted with a low viscosity, high strength cementitious grout.

1.3 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

¹ This test method is under the jurisdiction of ASTM Committee F17 on Plastic Piping Systems and is the direct responsibility of Subcommittee F17.67 on Trenchless Plastic Pipeline Technology.

Current edition approved April 1, 2019. Published September 2019. Originally approved in 2013. Last previous edition approved in 2013 as F2984–13. DOI: 10.1520/F2984-13R19.

2. Referenced Documents

2.1 *ASTM Standards*:²

D618 Practice for Conditioning Plastics for Testing

D883 Terminology Relating to Plastics

D1600 Terminology for Abbreviated Terms Relating to Plastics

D1784 Specification for Rigid Poly(Vinyl Chloride) (PVC) Compounds and Chlorinated Poly(Vinyl Chloride) (CPVC) Compounds

D2122 Test Method for Determining Dimensions of Thermoplastic Pipe and Fittings

D2152 Test Method for Adequacy of Fusion of Extruded Poly(Vinyl Chloride) (PVC) Pipe and Molded Fittings by Acetone Immersion

F412 Terminology Relating to Plastic Piping Systems

G195 Guide for Conducting Wear Tests Using a Rotary Platform Abraser

3. Terminology

3.1 *General*—Definitions are in accordance with Terminology D883 and Terminology F412. Abbreviations are in accordance with Terminology D1600, unless otherwise indicated.

3.2 *Definitions of Terms Specific to This Standard*:

3.2.1 See Fig. 1 to clarify terminology.

3.2.2 *PVC liner, n*—a tubular assembly field fabricated from injection molded PVC profile wall segments which are assembled into rings which are subsequently joined together which substantially conforms to the shape of the inner surface of the existing pipe structure or conduit over some portion of or its entire inner circumference.

3.2.3 *PVC segmental panels, n*—an element available in various geometries, consisting of a smooth inner surface and a ribbed outer surface (profile) with edge configurations to allow mechanical locking and sealing with adjacent panels.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

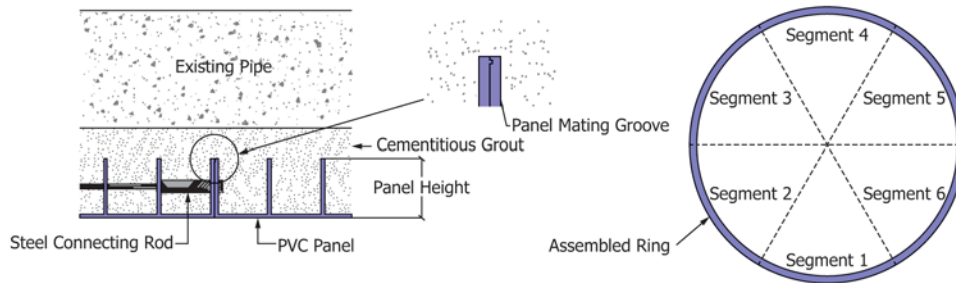


FIG. 1 Segmental Panel System Features

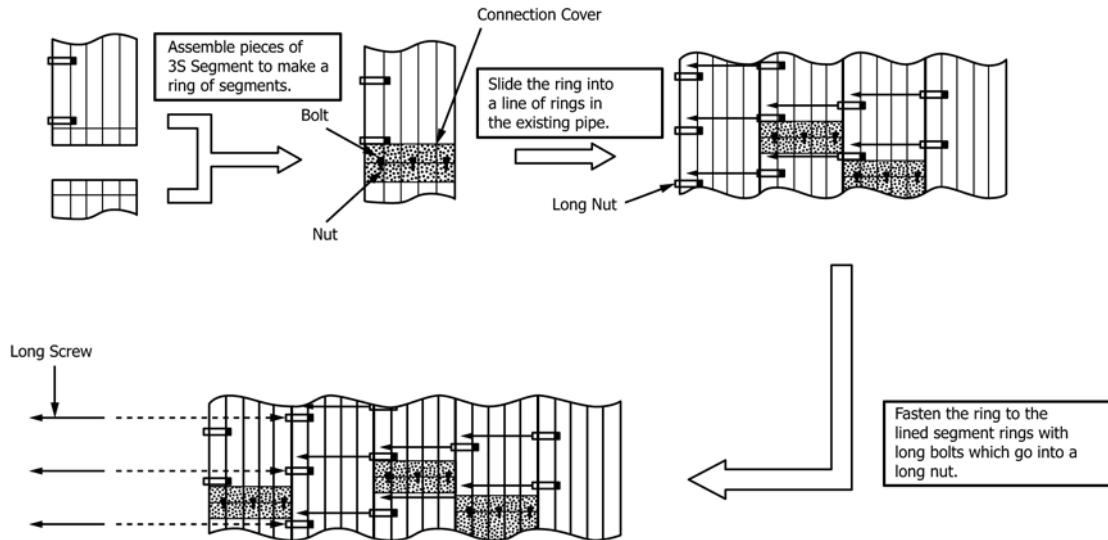


FIG. 2 Details of Fastening the Panel Segments into Rings and the Rings into the Tubular Shell

4. Materials and Manufacture

4.1 The molded panel segments shall be made from a PVC compound meeting all of the requirements for a cell classification of 12344 or higher as defined in Specification **D1784**.

4.2 The sealant material shall be a polyurethane, mono-liquid, moisture setting type flexible gasket that can be applied to the grooved mating faces of the segmental pieces prior to assembly.

4.3 The connecting hardware (connecting screw rods, nuts, and bolts) shall be made of a low carbon, general purpose steel meeting the SAE designation 1020 that has uni-chrome plating applied, or equivalent.

4.4 *Rework Material*—Clean rework PVC material generated from the manufacturer’s own production process may be used in the processing of new pieces provided that the finished product meets all the requirements of this specification.

5. Other Requirements

5.1 *Abrasion Resistance*—The resistance to abrasion of the finished panel materials shall be equivalent to or exceeding that of other PVC sewer pipeline specifications for applications in sanitary and storm sewer systems. In lieu of no abrasion performance requirements being stated in any of the existing PVC pipe standards, abrasion performance shall be obtained by

taking a minimum of three samples of the molded panel per production run and abrading the interior wall surface using a Taber Abrasion Test Method as given in referenced Guide **G195**. The testing shall be done employing an H18 wheel with an applied test load of 1000 grams. The abrasion speed shall be set at 60 revolutions per minute and the test shall be conducted for 1000 continuous revolutions. The test specimens shall be tested at 73.4 ± 3.6 °F (23 ± 2 °C) in an environment where the relative humidity is 50 ± 5 %. Materials deemed acceptable shall have an average mass change/loss for the sample set tested of less than 250 mg.

5.2 *Flexibility of the Assembled Rings*—The flexibility or ring stiffness of the assembled PVC panel segment rings shall be sufficient to allow for the grout’s placement in approximately five to six lifts. The flexibility factor, FF, shall be equal to or greater than 0.05. The FF is defined as the span (or diameter) squared divided by EI of the subject panel segment.

5.3 *Joint Leakage*—Water tightness at the connection of one panel segment with another panel segment shall be qualified by performing both an internal and an external test of the joint with the sealant applied. The joint shall show no leakage when a water pressure of 43.5 psi (0.3 MPa) is exerted either internally or externally on the joint for a period of 3 min. This is a qualification test that shall be performed for each new PVC