



Standard Guide for Evaluation of Aqueous Polymer Quenchants¹

This standard is issued under the fixed designation D 6666; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This guide provides information, without specific limits, for selecting standard test methods for testing aqueous polymer quenchants for initial qualification, determining quality, and the effect of aging.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory requirements prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

- D 95 Test Method for Water in Petroleum Products and Bituminous Materials by Distillation
- D 445 Test Method for Kinematic Viscosity of Transparent and Opaque Liquids (and Calculation of Dynamic Viscosity)
- D 892 Test Method for Foaming Characteristics of Lubricating Oils
- D 1744 Standard Test Method for Determination of Water in Liquid Petroleum Products by Karl Fischer Reagent³
- D 1747 Test Method for Refractive Index of Viscous Materials
- D 1796 Test Method for Water and Sediment in Fuel Oils by the Centrifuge Method (Laboratory Procedure)
- D 2624 Test Methods for Electrical Conductivity of Aviation and Distillate Fuels
- D 3519 Test Method for Foam in Aqueous Media (Blender Test)
- D 3601 Test Method for Foam In Aqueous Media (Bottle Test)
- D 3867 Test Methods for Nitrite-Nitrate in Water
- D 4327 Test Method for Anions in Water by Chemically Suppressed Ion Chromatography

- D 5296 Test Method for Molecular Weight Averages and Molecular Weight Distribution of Polystyrene by High Performance Size-Exclusion Chromatography
- D 6482 Test Method for Determination of Cooling Characteristics of Aqueous Polymer Quenchants by Cooling Curve Analysis with Agitation (Tensi Method)
- D 6549 Test Method for Determination of Cooling Characteristics of Quenchants by Cooling Curve Analysis with Agitation (Drayton Unit)
- E 70 Test Method for pH of Aqueous Solutions With the Glass Electrode
- E 979 Practice for Evaluation of Antimicrobial Agents as Preservatives for Invert Emulsion and Other Water Containing Hydraulic Fluids
- E 2275 Practice for Evaluating Water-Miscible Metalworking Fluid Bioresistance and Antimicrobial Pesticide Performance

3. Terminology

3.1 Definitions of Terms Specific to This Standard:

3.1.1 *austenite, n*—solid solution of one or more elements in face-centered cubic iron (gamma iron) and unless otherwise designated, the solute is generally assumed to be carbon **(1)**.⁴

3.1.2 *austenitizing, n*—forming austenite by heating a ferrous alloy into the transformation range (partial austenitizing) or above the transformation range (complete austenitizing). When used without qualification, the term implies complete austenitizing **(1)**.

3.1.3 *aqueous polymer quenchant, n*—a solution containing water, and one or more water-soluble polymers including poly(alkylene glycol), poly(vinyl pyrrolidone), poly(sodium acrylate), and poly(ethyl oxazoline) **(2, 3)** and additives for corrosion and foam control, if needed.

3.1.4 *biodegradation, n*—the process by which a substrate is converted by biological, usually microbiological, agents into simple, environmentally acceptable derivatives. **(4)**

3.1.5 *biodeterioration, n*—loss of product quality and performance and could be regarded as the initial stages of biodegradation (see 3.1.4), but in the wrong place at the wrong time, that is when the product is stored or in use. **(4)**

3.1.6 *convective cooling, n*—after continued cooling, and the interfacial temperature between the cooling metal and the

⁴ The boldface numbers in parentheses refer to the list of references at the end of this standard.

¹ This guide is under the jurisdiction of ASTM Committee D02 on Petroleum Products and Lubricants and is the direct responsibility of Subcommittee D02.L0.06 on Non-Lubricating Process Fluids.

Current edition approved April 15, 2009. Published July 2009. Originally approved in 2001. Last previous edition approved in 2004 as D 6666 – 04.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Withdrawn.

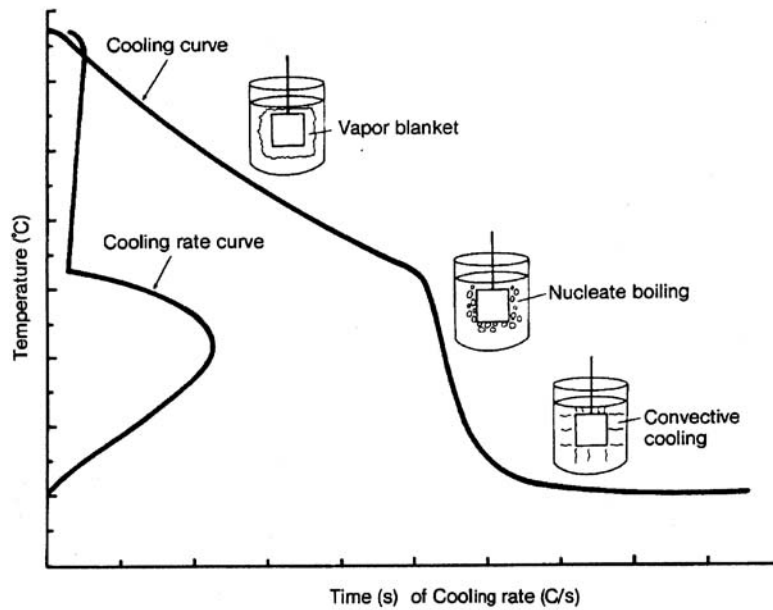


FIG. 1 Cooling Mechanisms of the Quenching Process

aqueous polymer quenchant is less than the boiling point of the water in the quenchant solution at which point cooling occurs by a convective cooling process. For convective cooling, fluid motion is due to density differences and the action of gravity and includes both natural motion and forced circulation (1, 5). This process is illustrated in Fig. 1.

3.1.7 *cooling curve, n*—a graphical representation of the cooling time (t)—temperature (T) response of the probe such as that shown in Fig. 1. (5)

3.1.8 *cooling curve analysis, n*—the process of quantifying the cooling characteristics of a quenchant medium based on the temperature versus time profile obtained by cooling a pre-heated metal probe assembly (see Fig. 2) under specified conditions which include: probe alloy and dimensions, probe and bath temperature, agitation rate, and aqueous polymer quenchant concentration.

3.1.9 *cooling rate curve, n*—obtained by calculating the first derivative (dT/dt) of the cooling time-temperature curve as illustrated in Fig. 1. (5)

3.1.10 *dragout, n*—solution carried out of a bath on the metal being quenched and associated handling equipment. (1)

3.1.11 *full-film boiling, n*—upon initial immersion of hot steel into a quenchant solution, a vapor blanket surrounds the metal surface resulting in full-film boiling as shown in Fig. 1. (5)

3.1.12 *nucleate boiling, n*—when the vapor blanket surrounding the hot metal collapses and a nucleate boiling process occurs as illustrated in Fig. 1. (5)

3.1.13 *quenchant medium, n*—any liquid or gas, or mixture, used to control the cooling of a metal to facilitate the formation of the desired microstructure and properties. (1)

3.1.14 *quench severity, n*—the ability of a quenchant medium to extract heat from hot metal. (6)

3.1.15 *transformation temperatures, n*—characteristic temperatures that are important in the formation of martensitic microstructure of steel including: A_{e1} —equilibrium austeniti-

zation phase change temperature; M_s —temperature at which transformation of austenite to martensite starts during cooling and M_f —temperature at which transformation of austenite to martensite is completed during cooling. (1)


4. Significance and Use

4.1 The significance and use of each test method will depend on the system in use and the purpose of the test method listed under Section 7. Use the most recent editions of the test methods.


5. Quenching Process

5.1 *Aqueous Polymer Quenchant Cooling Mechanisms*—Upon initial immersion of a heated metal into a solution of an aqueous polymer quenchant, an insulating polymer film, which controls the heat transfer rate from the hot metal into the cooler quenchant solution, forms around the hot metal which is separated by a vapor film (Fig. 3) (7) for the quenching process in a poly(alkylene glycol) quenchant. The overall heat transfer mediating properties of the film are dependent on both the film thickness (a function of polymer concentration) and interfacial film viscosity (a function of polymer type and bath temperature). The timing of film formation and subsequent film rupture and removal is dependent on the film strength of the polymer, agitation (both direction and mass flow), and turbulence of the polymer solution surrounding the cooling metal.

5.1.1 The cooling process that occurs upon initial immersion of the hot metal into the aqueous polymer quenchant is full-film boiling. This is frequently referred to as the vapor blanket stage. Cooling is slowest in this region. When the metal has cooled sufficiently, the polymer film encapsulating the hot metal ruptures and a nucleate boiling process results. The temperature at the transition from full-film boiling to nucleate boiling is called the Leidenfrost temperature. Cooling is fastest in this region. When the surface temperature of the cooling metal is less than the boiling temperature of water, convective

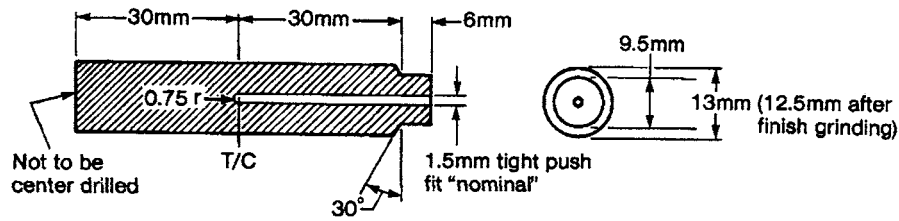

(a) Probe details

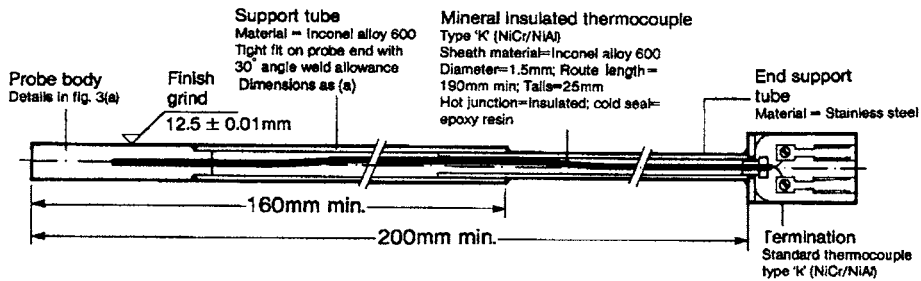

(b) General assembly

NOTE—From Wolfson Engineering Group Specification, available from Wolfson Heat Treatment Centre, Aston University, Aston Triangle, Birmingham B4 7ET, England, 1980.

FIG. 2 Schematic Illustration of the Probe Details and Probe Assembly

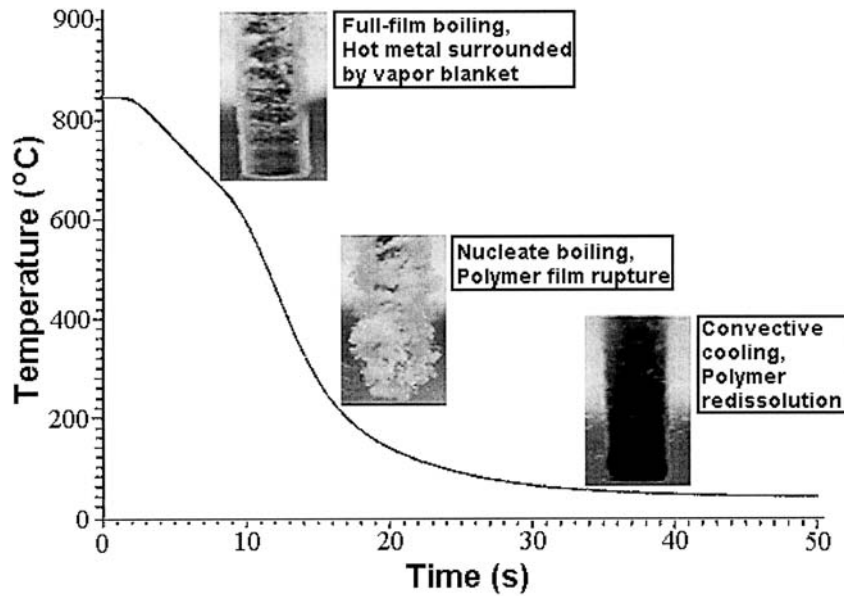


FIG. 3 Illustration of the Three Phases of Cooling

cooling results. All three cooling mechanisms are superimposed on a cooling curve and illustrated in Fig. 3. (7)

6. Sampling

6.1 Sampling—Flow is never uniform in agitated quench tanks. There is always variation of flow rate and turbulence

from top to bottom and across the tank. This means there may be significant variations of particulate contamination including carbon from the heat treating process and metal scale. For uniform sampling, a number of sampling recommendations have been developed.