



# Standard Specification for Electrodeposited Coatings on Threaded Fasteners (Unified Inch Screw Threads (UN/UNR))<sup>1</sup>

This standard is issued under the fixed designation F1941; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## INTRODUCTION

This specification covers the coating of steel unified inch screw threaded fasteners by electrodeposition. The properties of the coatings shall conform to the ASTM standards for the individual finishes listed.

Coating thickness values are based on the tolerances for 1A and 2A external Unified Inch Screw Threads. The coating must not cause the basic thread size to be transgressed by either the internal or external threads. The method of designating coated threads shall comply with ASME B1.1.

With normal methods for depositing metallic coatings from aqueous solutions, there is a risk of delayed failure due to hydrogen embrittlement for case hardened fasteners and fasteners having a hardness 40 HRC or above. Although this risk can be managed by selecting raw materials suitable for the application of electrodeposited coatings and by using modern methods of surface treatment and post heat-treatment (baking), the risk of hydrogen embrittlement cannot be completely eliminated. Therefore, the application of a metallic coating by electrodeposition is not recommended for such fasteners.

## 1. Scope\*

1.1 This specification covers application, performance and dimensional requirements for electrodeposited coatings on threaded fasteners with unified inch screw threads. It specifies coating thickness, supplementary hexavalent chromate or non-hexavalent passivate finishes, corrosion resistance, precautions for managing the risk of hydrogen embrittlement and hydrogen embrittlement relief for high-strength and surface-hardened fasteners. It also highlights the differences between barrel and rack plating and makes recommendations as to the applicability of each process.

1.2 The values stated in inch-pound units are to be regarded as standard. No other units of measurement are included in this standard.

1.3 The following precautionary statement pertains to the test method portion only, Section 9, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee F16 on Fasteners and is the direct responsibility of Subcommittee F16.03 on Coatings on Fasteners.

Current edition approved Dec. 15, 2010. Published January 2011. Originally approved in 1998. Last previous edition approved in 2007 as F1941 – 07. DOI: 10.1520/F1941-10.


## 2. Referenced Documents

2.1 *ASTM Standards*:<sup>2</sup>

- B117 Practice for Operating Salt Spray (Fog) Apparatus
- B487 Test Method for Measurement of Metal and Oxide Coating Thickness by Microscopical Examination of Cross Section
- B499 Test Method for Measurement of Coating Thicknesses by the Magnetic Method: Nonmagnetic Coatings on Magnetic Basis Metals
- B504 Test Method for Measurement of Thickness of Metallic Coatings by the Coulometric Method
- B567 Test Method for Measurement of Coating Thickness by the Beta Backscatter Method
- B568 Test Method for Measurement of Coating Thickness by X-Ray Spectrometry
- B659 Guide for Measuring Thickness of Metallic and Inorganic Coatings
- D6492 Practice for Detection of Hexavalent Chromium on Zinc and Zinc/Aluminum Alloy Coated Steel
- E376 Practice for Measuring Coating Thickness by Magnetic-Field or Eddy-Current (Electromagnetic) Examination Methods

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard.

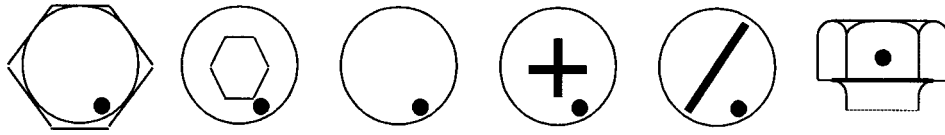

NOTE 1—Black dot (•) indicates test surface.

FIG. 1 Significant Surfaces on Externally Threaded Fasteners

F606 Test Methods for Determining the Mechanical Properties of Externally and Internally Threaded Fasteners, Washers, Direct Tension Indicators, and Rivets

F1470 Practice for Fastener Sampling for Specified Mechanical Properties and Performance Inspection

F1624 Test Method for Measurement of Hydrogen Embrittlement Threshold in Steel by the Incremental Step Loading Technique

F1940 Test Method for Process Control Verification to Prevent Hydrogen Embrittlement in Plated or Coated Fasteners

2.2 ASME Standard:<sup>3</sup>

B1.1 Unified Inch Screw Threads (UN and UNR Thread Form)

2.3 National Aerospace Standard (AIA):<sup>4</sup>

NASM-1312-5 Fast Test Method - Method 5: Stress Durability

2.4 IFI Standard:<sup>5</sup>

IFI-142 Hydrogen Embrittlement Risk Management

### 3. Terminology

#### 3.1 Definitions:

3.1.1 *local thickness*—the mean of the thickness measurements, of which a specified number is made within a reference area.


3.1.2 *minimum local thickness*—the lowest local thickness value on the significant surface of a single article.

3.1.3 *reference area*—the area within which a specified number of single measurements are required to be made.

3.1.4 *significant surface*—significant surfaces are areas where the minimum thickness to be met shall be designated on the applicable drawing or by the provision of a suitably marked sample. However, if not designated, significant surfaces shall be defined as those normally visible, directly or by reflection, which are essential to the appearance or serviceability of the fastener when assembled in normal position, or which can be the source of corrosion products that deface visible surfaces on the assembled fastener. Figs. 1 and 2 illustrate significant surfaces on standard externally threaded and internally threaded fasteners.

### 4. Classification

4.1 *Coating Material*— The coating material shall be selected and designated in accordance with Table 1.

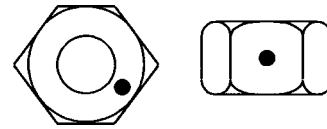

NOTE 1—Black dot (•) indicates test surface.

FIG. 2 Significant Surfaces on Internally Threaded Fasteners

TABLE 1 Designation of Common Coating Materials

Coating Designation	Coating Type
Fe/Zn	Zinc
Fe/Cd	Cadmium
Fe/Zn-Co	Zinc Cobalt Alloy
Fe/Zn-Ni	Zinc Nickel Alloy
Fe/Zn-Fe	Zinc Iron Alloy

4.2 *Coating Thickness*—The coating thickness shall be selected and designated in accordance with Table 2:

4.3 *Chromate Finish*—When not specified, the hexavalent, trivalent or other chromiate finish shall be used at the option of the manufacturer and its appearance shall be selected in accordance with the designation selected in Table 3.

4.3.1 *Passivate*—for the purpose of this specification, a conversion coating shall not contain hexavalent chromium.

4.3.1.1 *Trivalent Chromite Passivate Finish*—Unless otherwise specified, the typical appearance of the trivalent chromite finish shall be transparent, colorless and shall not be subjected to the requirements of typical appearance as determined in Table 3. In addition, the classification code to be used shall be appended with the letter "T" (for example, Fe/Zn 5CT, as defined in Table A1.1).

4.3.1.2 *Supplemental Passivate Finish*—Unless otherwise specified, the typical appearance of the supplemental passivate finish shall be transparent, colorless and shall not be subjected to the requirements of typical appearances as determined in Table 3. In addition, the classification code to be used shall be appended with the letter "S" (for example Fe/Zn 5AS). Other colored finishes may be specified at time of purchase. Requirements of the other colored finishes to be agreed upon at time of purchase.

TABLE 2 Designation of Coating Thickness

NOTE 1—The conversion factor from inch to microns is  $2.54 \times 10^4$  (for example, 0.0001 in. = 2.54  $\mu$ m).

Thickness Designation	Minimum Thickness in.
3	0.0001
5	0.0002
8	0.0003
12	0.0005

<sup>3</sup> Available from American Society of Mechanical Engineers (ASME), ASME International Headquarters, Three Park Ave., New York, NY 10016-5990, http://www.asme.org.

<sup>4</sup> Available from Standardization Documents Order Desk, DODSSP, Bldg. 4, Section D, 700 Robbins Ave., Philadelphia, PA 19111-5098.

<sup>5</sup> Available from Industrial Fasteners Institute (IFI), 1717 East 9th Street, Suite 1105, Cleveland, OH 44114-2879.

**TABLE 3 Designation of Chromate Finish**

NOTE 1—Coated fasteners with trivalent chromite ( $\text{Cr}^{+3}$ ) are not subjected to the required yellow, opaque, and black color. See [Appendix X5](#)

NOTE 2—When fasteners are coated with trivalent chromite ( $\text{Cr}^{+3}$ ) the classification code to be used shall be appended with the letter "T".

Designation	Type	Typical Appearance
A	Clear	Transparent colorless with slight iridescence
B	Blue-bright	Transparent with a bluish tinge and slight iridescence
C	Yellow	Yellow iridescent
D	Opaque	Olive green, shading to brown or bronze
E	Black	Black with slight iridescence
F	Organic	Any of the above plus organic topcoat

NOTE 1—The use of supplemental passivated finishes are technically not "chromate" films and they do not contain hexavalent chromium ions, they are supplemental coatings that render the active zinc surface passive and provide protection to the steel fastener.

## 5. Ordering Information for Electroplating

5.1 When ordering threaded fasteners to be coated by electrodeposition in accordance with this specification, the following information shall be supplied to the electroplater:

5.1.1 The desired coating, coating thickness, the chromate or passivate finish, the color and appearance (if applicable), or the classification codes as specified in [Tables 1-3](#). (for example, Fe/Zn 5C denotes yellow zinc plated with a minimum thickness of 0.0002 in. on significant surfaces.)

5.1.2 The identification of significant surfaces (optional).

5.1.3 The requirement, if any, for stress relief before electroplating, in which case the stress-relief conditions must be specified.

5.1.4 The requirements, if any, for hydrogen embrittlement relief by heat treatment (baking) stating the tensile strength or surface hardness of the fasteners and/or baking time and temperature.

NOTE 2—Fasteners with a specified maximum hardness of 34 HRC and below have a very low susceptibility to hydrogen embrittlement and do not require baking.

5.1.5 The requirements, if any, for the type of electroplating process (barrel-plating or rack-plating). See [Section 10](#) and [Appendix X1](#).

5.1.6 The designation of coated thread class shall comply with [ASME B1.1](#).

## 6. Requirements

6.1 *Coating Requirements*—The electrodeposited coating as ordered shall cover all surfaces and shall meet the following requirements:

6.1.1 The coating metal deposit shall be bright or semi-bright unless otherwise specified by the purchaser, smooth, fine grained, adherent and uniform in appearance.

6.1.2 The coating shall be free of blisters, pits, nodules, roughness, cracks, unplated areas, and other defects that will affect the function of the coating.

6.1.3 The coating shall not be stained, discolored or exhibit any evidence of white or red corrosion products.

6.1.3.1 Slight discoloration that results from baking, drying, or electrode contact during rack-plating, or all of these, as well as slight staining that results from rinsing shall not be cause for rejection.

6.2 *Corrosion Resistance*—Coated fasteners, when tested by continuous exposure to neutral salt spray in accordance with [9.3](#), shall show neither corrosion products of coatings (white corrosion) nor basis metal corrosion products (red rust) at the end of the test period. The appearance of corrosion products visible to the unaided eye at normal reading distance shall be cause for rejection, except when present at the edges of the tested fasteners. Refer to [Annex A1](#) for neutral salt spray performance requirements for zinc, zinc alloy and cadmium coatings.

6.3 *Thickness*—The coating thickness shall comply with requirements of [Table 2](#) when measured in accordance with [9.1](#).

6.3.1 *Restrictions on Coating Thickness*—This specification imposes minimum local thickness requirements at significant surfaces in accordance with [Table 2](#). Thick or thin local thickness in a location other than a significant surface shall not be a cause for rejection. However the following restrictions apply:

6.3.1.1 Minimum coating thickness at low current density areas, such as the center of a bolt or recesses, must be sufficient to provide for adequate chromate adhesion.

6.3.1.2 *External Threads*— Maximum coating thickness at high current density threaded tips must provide for class 3A GO thread gauge acceptance.

6.3.1.3 *Internal Threads*— Maximum coating thickness of internal threads must provide for class 1B, 2B, or 3B Go thread gauge acceptance.

6.3.1.4 Surfaces such as threads, holes, deep recesses, bases of angles, and similar areas on which the specified thickness of deposit cannot readily be controlled, are exempted from minimum thickness requirements unless they are specially designated as not being exempted. When such areas are subject to minimum thickness requirements, the purchaser and the manufacturer shall recognize the necessity for either thicker deposits on other areas or special racking.

6.3.2 *Applicability to Unified Inch Screw Threads:*

6.3.2.1 The applicability of the required coating to unified inch screw threads is limited by the basic deviation of the threads, and hence limited by the pitch diameter, allowance and tolerance positions. Refer to [Appendix X3](#) as a guideline for the tolerances of the various thread sizes and classes and the coating thickness they will accommodate.

6.3.2.2 Because of the inherent variability in coating thickness by the barrel-plating process, the application of a minimum coating thickness of 0.0005 in. is not recommended for a standard screw thread by this method due to the fact that dimensional allowance of most threaded fasteners normally does not permit it. If the size of the fastener is large enough to economically use the rack-plating process, then the latter shall be used to obtain this thickness requirement. If heavier coatings are required allowance for the deposit buildup must be made during the manufacture of fasteners.